

Separation of CO₂-CH₄ and CO₂-N₂ Systems Using Ion-exchanged FAU-type Zeolite Membranes with Different Si/Al Ratios

Yasuhisa Hasegawa, Takeshi Tanaka, Kaori Watanabe, Byeong-Heon Jeong,
Katsuki Kusakabe[†] and Shigeharu Morooka

Department of Applied Chemistry, Kyushu University, Fukuoka 812-8581, Japan
(Received 23 July 2001 • accepted 14 September 2001)

Abstract—FAU-type zeolite membranes with different Si/Al ratios were hydrothermally synthesized on the outer surface of a porous α -Al₂O₃ support tube. The permeances of the membranes to CO₂, CH₄ and N₂ were then measured at 308 K for single-component and equimolar binary systems. The separation properties were dependent on both the Si/Al ratio and the ion-exchange treatment. For single-component systems, a lower Si/Al ratio resulted in the incorporation of a larger number of Na⁺ ions. For a CO₂-CH₄ mixture, both CO₂ permeances and CO₂/CH₄ selectivities were approximately half the values obtained for a binary CO₂-N₂ mixture. The highest selectivities, obtained using the NaX(1) zeolite membrane, were 28 for CO₂/CH₄ and 78 for CO₂/N₂. The RbY, RbX(1) and RbX(2) zeolite membranes showed larger CO₂ permeances, compared with those of the original Na-type membranes. Ion-exchange with K⁺ ions was the most effective for the NaY zeolite membrane in that both the CO₂ permeance and the CO₂/CH₄ selectivity were increased.

Key words: FAU-type Zeolite, Membrane, Ion Exchange, Gas Separation, Selectivity

INTRODUCTION

Zeolite membranes have considerable potential for use in the separation of small-sized molecules, and a number of studies have been reported for MFI [Aoki et al., 2000a; Dong et al., 2000; Gump et al., 2000; Lai et al., 2000; Matsufuji et al., 2000a; Millot et al., 2000; Nelson et al., 2001; Noack et al., 2000; Pan and Lin, 2001; Tuan et al., 2000; Van de Graaf et al., 2000; Xomeritakis et al., 2000], LTA [Aoki et al., 2000b; Okamoto et al., 2001; Xu et al., 2000], FAU [Hasegawa et al., 2001; Kita et al., 2000; Li et al., 2001; Nikolakis et al., 2001], MOR [Bernal et al., 2000; Lin et al., 2000], FER [Matsufuji et al., 2000b], SAPO-34 [Poshusta et al., 2000, 2001] and MCM-48 [Nishiyama et al., 2001] membranes. The FAU-type zeolite has relatively large pores, which are composed of 12-membered oxygen rings of approximately 0.74 nm in diameter. Thus, FAU-type zeolite membranes do not show strict molecular-sieving properties, as do the MFI-types, and separation by FAU-type zeolite membranes is usually achieved by differences in the adsorptivities of permeates. The larger pores of FAU-type zeolite membranes are, however, beneficial for higher permeation rates, compared to the MFI- and LTA-type zeolite membranes.

The FAU-type zeolite includes X- and Y-types, Si/Al ratios of which are 1-1.5 and 1.5-3.0, respectively. Thus, the number of cations, which can be coordinated in the X-type structure, is larger than that in the Y-type structure. Kusakabe et al. [1997, 1998] prepared NaY and NaX zeolite membranes on porous α -Al₂O₃ support tubes and investigated their properties in terms of the separation of CO₂ from N₂. The CO₂/N₂ selectivity reached a maximum of approximately 100 for the NaY-type zeolite membrane at a permeation temperature of 308 K. Permeance to CO₂ decreased with

a decrease in the Si/Al ratio. Kusakabe et al. [1998, 1999] further investigated the permeation properties of Y-type zeolite membranes, which had been ion-exchanged with alkali and alkali-earth cations. The Y-type zeolite membranes, ion-exchanged with K⁺, Rb⁺, Cs⁺ and Mg²⁺ ions, showed high CO₂/N₂ selectivities, compared to NaY-type zeolite membranes.

Vapor permeation [Kita et al., 2000; Jeong et al., 2001] and pervaporation [Kita et al., 2000; Li et al., 2001] of organic compounds have also been studied using FAU-type zeolite membranes. Nikolakis et al. [2001] separated a benzene-cyclohexane mixture using an NaX-type zeolite membrane and obtained the maximum benzene/cyclohexane selectivity of 160 at 373 K with a benzene permeation flux of 0.27 mmol·m⁻²·s⁻¹. Similar results were reported by Kita et al. [2000] and Jeong et al. [2001]. Nikolakis et al. [2001] attributed the high permeation selectivity to the adsorption selectivity of the permeates on the feed-side surface of the membrane. However, Jeong et al. [2001] showed that the adsorption selectivity on the feed-side surface of the membrane was not a major factor. Thus, the interactions of pore walls and permeating molecules are important for the permeation selectivities of FAU-type zeolite membranes, but the mechanism is not fully understood.

In the present study, we report on the preparation of FAU-type zeolite membranes with different Si/Al ratios on the outer surface of α -Al₂O₃ support tubes by means of a hydrothermal synthesis. The membranes were ion-exchanged with Rb⁺ and K⁺ ions, and their permeation properties were investigated by using equimolar mixtures of CO₂-CH₄ and CO₂-N₂ at 308 K. The role of the interactions between the pore walls and permeating molecules was then discussed.

EXPERIMENTAL

FAU-type zeolite membranes were prepared on the outer sur-

[†]To whom correspondence should be addressed.

E-mail: kusaktcf@mbox.nc.kyushu-u.ac.jp

face of porous α - Al_2O_3 support tubes (NOK Corp., Japan) by the same procedures as were reported previously [Hasegawa et al., 2001; Kusakabe et al., 1999]. The properties of the support tube were: length=200 mm; outside diameter=2.1 mm; inside diameter=1.7 mm; void fraction=0.39; and pore size=120–150 nm. A solution used for synthesis was prepared by mixing water glass, NaAlO_2 and NaOH . The composition of the starting solution was $\text{Al}_2\text{O}_3 : \text{SiO}_2 : \text{Na}_2\text{O} : \text{H}_2\text{O} = 1 : x : 17 : 975$, where the SiO_2 ratio, x , was 12.8 for NaY-type zeolite [Hasegawa et al., 2001], 6.4 and 4.8 for NaX-type zeolites. Hereafter, the samples, which were prepared using these solutions, are referred to as NaY-, NaX(1)- and NaX(2)-type zeolites, respectively. The solution was stirred for 4 h at room temperature prior to the synthesis. The outer surface of the support tube was rubbed with NaX zeolite particles (Tosoh Corp., #F-9; $\text{Si}/\text{Al}=1.25$, crystal size=3–5 μm). The seeded alumina tube was then placed into a tubular autoclave, which was filled with the synthesis solution. This autoclave was then horizontally positioned into an oven, and kept at 363 K for 24 h. The prepared zeolite membranes were ion-exchanged with a 0.10 mol·L⁻¹ solution of either KCl or RbCl, rinsed with deionized water, and then air-dried. NaY, NaX(1) and NaX(2) zeolite particles were also prepared under the same conditions as were used for the synthesis of the membranes. The Si/Al ratio and the degree of ion-exchange were determined by energy-dispersive X-ray analysis (EDX, Kevex Delta Class).

Permeation tests [Kusakabe et al., 1997] were carried out using single-component CO_2 , CH_4 and N_2 , as well as equimolar mixtures of CO_2 - CH_4 and CO_2 - N_2 . Helium was used as a sweep gas. The total pressure of both sides of the membrane was maintained at 101.3 kPa, and the permeation temperature was fixed at 308 K throughout the experiments. Permeance was calculated from the following equation.

$$\text{Permeance} = \frac{(\text{mol of gas transferred per unit time})}{(\text{membrane area})(\text{partial pressure difference})} \quad (1)$$

The selectivity was defined by the ratio of permeances. The isotherms of single-component CO_2 , CH_4 and N_2 were determined using an adsorption unit (Bell Japan, FMS-BG). The micropore size distributions were decided by an adsorption method (Micromeritics, ASAP2001).

RESULTS AND DISCUSSION

The formation of the FAU-type structure was confirmed based on XRD by Kusakabe et al. [1997]. The Si/Al ratios, as determined by EDX, were 1.54 for NaY, 1.26 for NaX(1) and 1.16 for NaX(2) zeolite samples. Each membrane consisted of two zeolite layers [Kusakabe et al., 1997]: an inner layer formed in the voids of the support (ca. 5 μm in thickness) and an outer layer formed on the surface (ca. 3 μm in thickness). For all membranes, the top surface was smooth.

Figs. 1(a) and (b) show the permeation data for CO_2 - CH_4 and CO_2 - N_2 for the FAU-type zeolite membranes, respectively. For all cases, CO_2 permeated faster than N_2 and CH_4 . This can be explained by the fact that CO_2 is adsorbed more strongly than CH_4 and N_2 as shown in Fig. 2, and by the smaller kinetic diameter (CO_2 : 0.33 nm, N_2 : 0.36 nm, CH_4 : 0.38 nm) [Breck, 1974]. The permeances were the highest for the NaY-type zeolite membrane and decreased with a decrease in the Si/Al ratio. However, the adsorptivities of CO_2

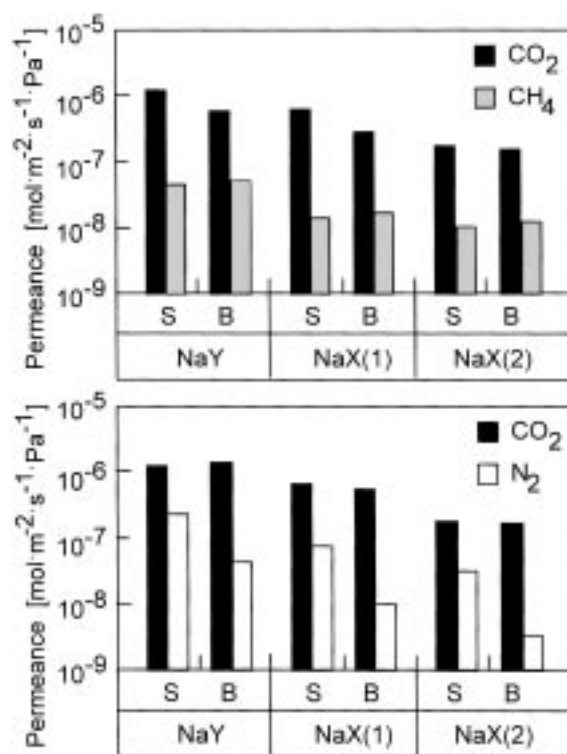


Fig. 1. Permeances through NaY-, NaX(1)- and NaX(2)-type zeolite membranes for (a) CO_2 - CH_4 and (b) CO_2 - N_2 systems.

S: Single-component; B: equimolar binary mixture

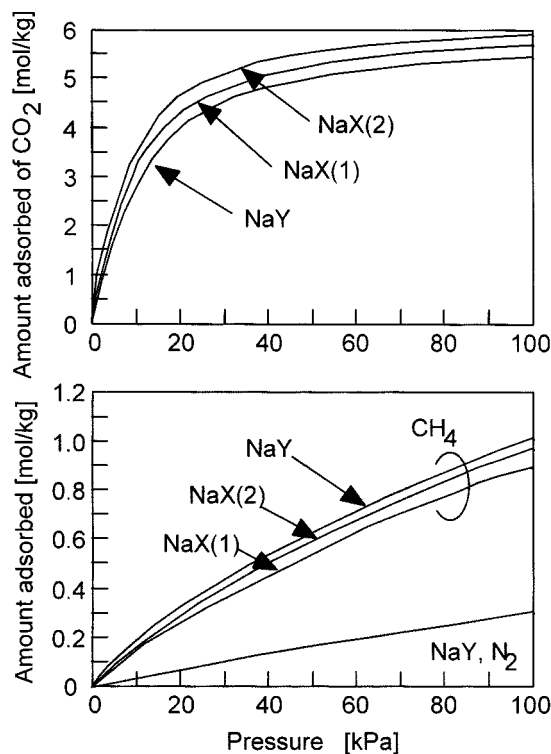


Fig. 2. Adsorption isotherms for single-component CO_2 , CH_4 and N_2 on NaY, NaX(1) and NaX(2) zeolite particles.

and CH_4 were not significantly influenced by the Si/Al ratio. The number of Na^+ ions which were originally incorporated in the zeolite

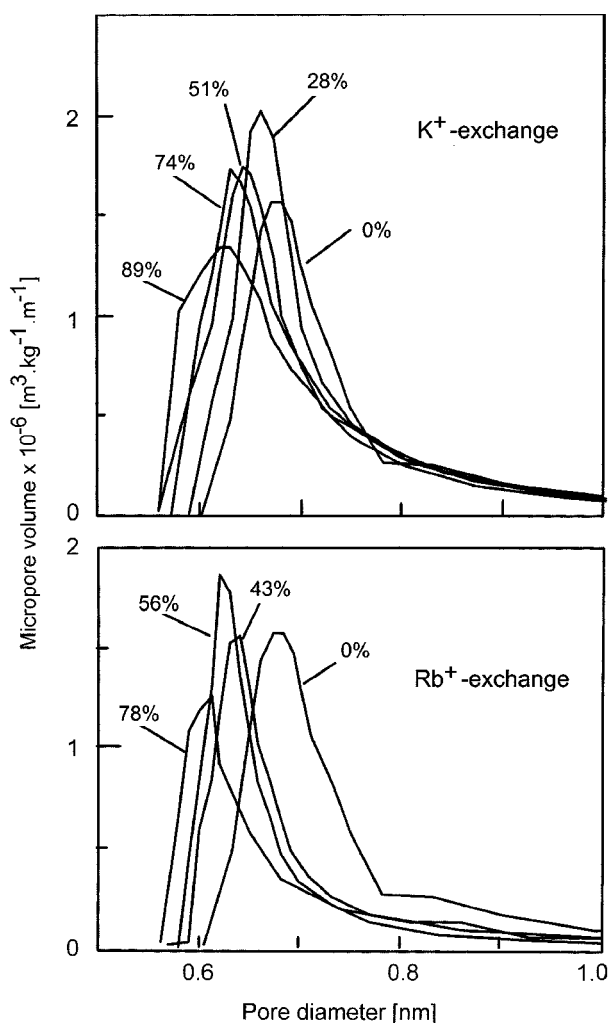


Fig. 3. Size distributions of micropores for K and Rb ion-exchanged zeolites. Numbers refer to the degree of ion-exchange.

structure was dependent on the Si/Al ratio, and was of the order of NaX(2)>NaX(1)>NaY. These results suggest that the permeation rates are related to the size of zeolitic pores, although the pores are larger than the permeating molecules as shown in Fig. 3.

The CO₂ permeance of the NaY-type zeolite membrane for the binary CO₂-N₂ system was larger, and the N₂ permeance was much smaller than those for single-component systems. However, the re-

verse tendencies were observed for the CO₂-CH₄ system; namely, the CO₂ permeance for the binary system was smaller than that for the single component system. As a result, the CO₂/CH₄ selectivity for the binary system was significantly low, compared to the ideal CO₂/CH₄ selectivity (ie., selectivity calculated from permeances for single-component systems), as indicated in Table 1. Kusakabe et al. [1997, 1998, 1999] reported that these results could be attributed to the preferential adsorption of CO₂ from the binary mixture of CO₂ and N₂. Similar permeation behaviors were obtained in the present study for the NaX(1)- and NaX(2)-type zeolite membranes. Furthermore, they explained the permeation properties using a sorption-diffusion model, and diffusion coefficients of CO₂ and N₂ were calculated. The diffusion coefficient of CO₂ was one order of magnitude smaller than that of N₂, because CO₂ was the strongly adsorbed component on zeolites. The reverse tendency of the CO₂/CH₄ selectivity was caused by diffusion coefficients.

Figs. 4(a) and (b) show the relationship between CO₂ permeances and CO₂ selectivities for the binary systems of CO₂-CH₄ and CO₂-N₂, respectively. The permeances and selectivities of CO₂ for the CO₂-CH₄ system were half the values found for the CO₂-N₂ system. When the NaX(1)-type zeolite membrane was used, the maximum selectivity was determined to be 28 for the CO₂-CH₄ system and 78 for the CO₂-N₂ system. The high CO₂/CH₄ selectivities of these FAU-type zeolite membranes (pore size=0.74 nm) were largely the result of the preferential adsorption of CO₂. Poshusta et al. [2000,

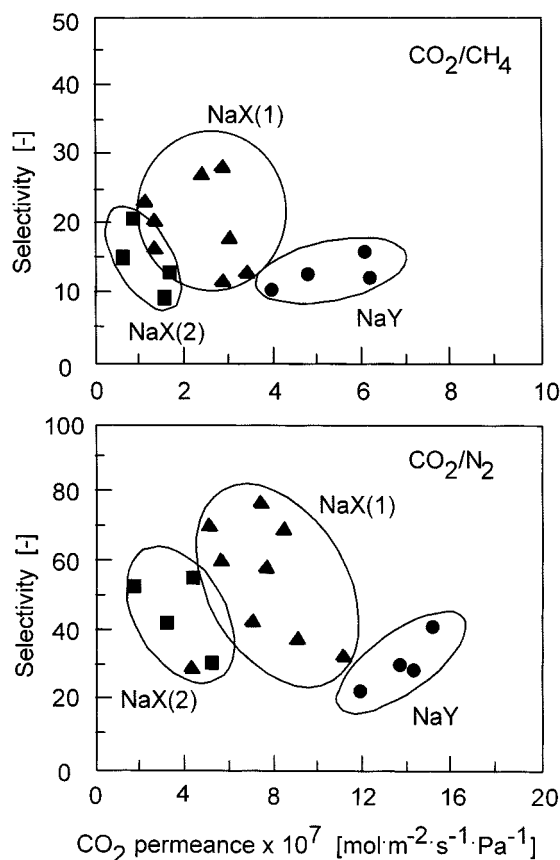


Fig. 4. Relationship between permeance and selectivity of CO₂ for NaY-, NaX(1)- and NaX(2)-type zeolite membranes for (a) CO₂-CH₄ and (b) CO₂-N₂ systems.

Table 1. CO₂ selectivities of FAU-type zeolite membranes with different Si/Al ratios

Membrane	Si/Al molar ratio	System	Selectivity	
			CO ₂ /CH ₄	CO ₂ /N ₂
NaY	1.54	Single	28	6
		Binary	12	30
NaX(1)	1.26	Single	51	9
		Binary	18	60
NaX(2)	1.16	Single	18	5
		Binary	13	53

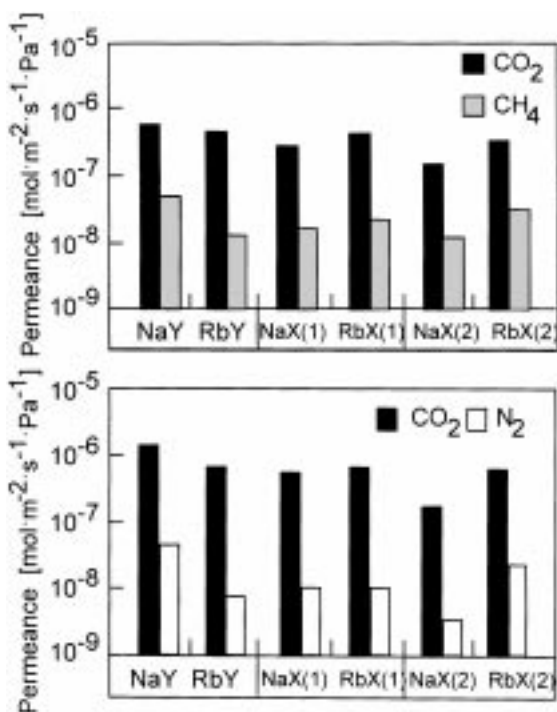


Fig. 5. Permeances through NaY-, RbY-, NaX(1)-, RbX(1)-, NaX(2)- and RbX(2)-type zeolite membranes for (a) CO_2 - CH_4 and (b) CO_2 - N_2 systems.

2001] synthesized an SAPO-34 zeolite membrane (pore size=0.4 nm), which was able to separate CO_2 from CH_4 . The highest selectivity was 36 for an equimolar mixture of CO_2 - CH_4 at 300 K. The single-component CO_2 permeance was $2.0 \times 10^{-7} \text{ mol} \cdot \text{m}^{-2} \cdot \text{s}^{-1} \cdot \text{Pa}^{-1}$ under the same conditions. Amorphous silica, which has smaller pores than the Y-type zeolite, is often used as the material for membranes. Silica membranes [De Vos and Verweij, 1998; Tsai et al., 2000] can recognize small gaseous molecules on the basis of their size, and H_2 and CO_2 permeate at higher rates than CH_4 and N_2 . Tsai et al. [2000] prepared dual-layer microporous silica membranes using a sol-gel method. The CO_2/CH_4 selectivity was 200 for an equimolar binary mixture at 299 K. However, the CO_2 permeance was relatively low ($10^{-7} \text{ mol} \cdot \text{m}^{-2} \cdot \text{s}^{-1} \cdot \text{Pa}^{-1}$), compared to that of Y-type zeolite membranes.

Figs. 5(a) and (b) show the effect of Rb^+ ions on permeation properties for equimolar CO_2 - CH_4 and CO_2 - N_2 systems, respectively. For the Y-type zeolite membrane, the permeances to CH_4 and N_2 greatly decreased by the ion-exchange treatment, and as a result, both CO_2/CH_4 and CO_2/N_2 selectivities increased. For the X(1)- and X(2)-type zeolite membranes, however, the permeance to all permeants increased. Thus, CO_2/CH_4 and CO_2/N_2 selectivities were not improved. Based on these results, the NaY-type zeolite membrane was ion-exchanged with K^+ , in an attempt to further increase the CO_2 selectivities. As shown in Figs. 6(a) and (b), both the CO_2 permeance and the CO_2 selectivity were improved. This suggests that the incorporation of K^+ ions caused a slight decrease in the zeolitic pores, and increased the adsorption of CO_2 . The CO_2 permeance and CO_2/CH_4 selectivity of the KY-type zeolite membrane was in the range of $(7.5\text{--}9.0) \times 10^{-7} \text{ mol} \cdot \text{m}^{-2} \cdot \text{s}^{-1} \cdot \text{Pa}^{-1}$ and 25–40, respectively. These values can be assumed to be suitable for CO_2 removal in com-

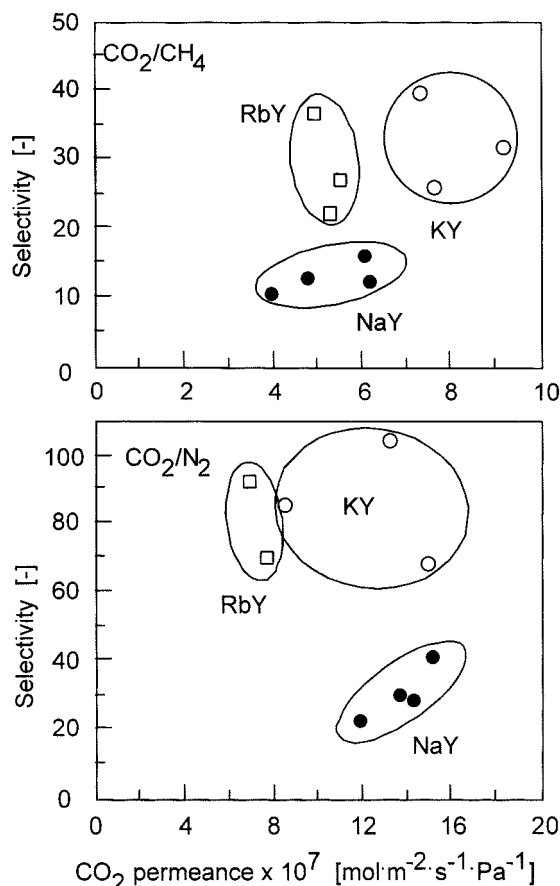


Fig. 6. Relationship between permeance and selectivity of CO_2 for NaY-, KY- and RbY-type zeolite membranes for (a) CO_2 - CH_4 and (b) CO_2 - N_2 systems.

mercial processes [Watanabe, 1999].

CONCLUSIONS

FAU-type zeolite membranes with different Si/Al ratios were prepared by means of a hydrothermal synthesis. Permeances for single-component systems at a temperature of 308 K were in the order of $\text{CO}_2 > \text{N}_2 > \text{CH}_4$, and decreased with decreasing Si/Al ratio. Permeances and selectivities of CO_2 for the CO_2 - CH_4 system were approximately half the values obtained for the CO_2 - N_2 system. The NaX(1)-type zeolite membrane showed the maximum CO_2 selectivities, which were 28 for the CO_2 - CH_4 system and 78 for the CO_2 - N_2 system, respectively. In an attempt to increase the CO_2 selectivity, the incorporated Na^+ ions were exchanged with Rb^+ . The effect of the ion-exchange was the highest for the NaY-type zeolite membrane. The CO_2 separation ability of the NaY-type zeolite membrane was further improved by ion-exchange with K^+ . The CO_2/CH_4 selectivity of the KY-type zeolite membrane was in the range of 25–40, and the CO_2 permeance was in the range of $(7.5\text{--}9.0) \times 10^{-7} \text{ mol} \cdot \text{m}^{-2} \cdot \text{s}^{-1} \cdot \text{Pa}^{-1}$.

ACKNOWLEDGEMENTS

This work was supported by the Japan Society for the Promo-

tion of the Science (JSPS) and the New Energy and Industrial Technology Development Organization (NEDO) of Japan. We sincerely acknowledge the support of NOK Corporation, Japan and Tosoh Corporation, Japan.

REFERENCES

- Aoki, K., Tuan, V. A., Falconer, J. L. and Noble, R. D., "Gas Permeation Properties of Ion-exchanged ZSM-5 Zeolite Membranes," *Micropor. Mesopor. Mater.*, **39**, 485 (2000a).
- Aoki, K., Kusakabe, K. and Morooka, S., "Separation of Gases with an A-Type Zeolite Membrane," *Ind. Eng. Chem. Res.*, **39**, 2245 (2000b).
- Bernal, M. P., Piera, E., Coronas, J., Menéndez, M. and Santamaría, J., "Mordenite and ZSM-5 Hydrophilic Tubular Membranes for the Separation of Gas Phase Mixtures," *Catalysis Today*, **56**, 221 (2000).
- Breck, D. W., "Zeolite Molecular Sieves," Wiley, New York (1974).
- De Vos, R. M. and Verweij, H., "Improved Performance of Silica Membranes for Gas Separation," *J. Membr. Sci.*, **143**, 37 (1998).
- Dong, J., Lin, Y. S., Hu, M. Z.-C., Peascoe, R. A. and Payzant, E. A., "Template-removal-associated Microstructural Development of Porous-ceramic-supported MFI Zeolite Membranes," *Micropor. Mesopor. Mater.*, **34**, 241 (2000).
- Gump, C. J., Lin, X., Falconer, J. L. and Noble, R. D., "Experimental Configuration and Adsorption Effects on the Permeation of C₄ Isomers through ZSM-5 Zeolite Membranes," *J. Membr. Sci.*, **173**, 35 (2000).
- Hasegawa, Y., Watanabe, K., Kusakabe, K. and Morooka, S., "The Separation of CO₂ Using Y-type Zeolite Membranes Ion-exchanged with Alkali Metal Cations," *Sep. Purif. Technol.*, **22-23**, 319 (2001).
- Jeong, B.-H., Hasegawa, Y., Kusakabe, K. and Morooka, S., "Separation of Benzene and Cyclohexane Mixtures Using an FAU-type Zeolite Membrane," Submitted to *Sep. Sci. Technol.*, (2001).
- Kita, H., Asamura, H., Tanaka, K. and Okamoto, K., "Preparation and Pervaporation Properties of X- and Y-Type Zeolite Membranes," ACS Symposium Series 744, Membrane Formation and Modification, American Chemical Society, Washington D.C., 330 (2000).
- Kusakabe, K., Kuroda, T., Murata, A. and Morooka, S., "Formation of a Y-type Zeolite Membrane on a Porous α -Alumina Tube for Gas Separation," *Ind. Eng. Chem. Res.*, **36**, 649 (1997).
- Kusakabe, K., Kuroda, T. and Morooka, S., "Separation of Carbon Dioxide from Nitrogen Using Ion-exchanged Faujasite-type Zeolite Membranes Formed on Porous Support Tubes," *J. Membr. Sci.*, **148**, 13 (1998).
- Kusakabe, K., Kuroda, T., Uchino, K., Hasegawa, Y. and Morooka, S., "Gas Permeation Properties of Ion-Exchanged Faujasite-Type Zeolite Membranes," *AIChE J.*, **45**, 1220 (1999).
- Lai, R. and Gavalas, G. R., "ZSM-5 Membrane Synthesis with Organic-free Mixtures," *Micropor. Mesopor. Mater.*, **38**, 239 (2000).
- Li, S., Tuan, V. A., Falconer, J. L. and Noble, R. D., "Separation of 1,3-Propanediol from Aqueous Solutions Using Pervaporation through an X-type Zeolite Membrane," *Ind. Eng. Chem. Res.*, **40**, 1952 (2001).
- Lin, X., Kikuchi, E. and Matsukata, M., "Preparation of Mordenite Membranes on α -alumina Tubular Supports for Pervaporation of Water-isopropyl Alcohol Mixtures," *Chem. Commun.*, 957 (2000).
- Matsufuji, T., Watanabe, K., Nishiyama, N., Egashira, Y., Matsukata, M. and Ueyama, K., "Permeation of Hexane Isomers through an MFI Membrane," *Ind. Eng. Chem. Res.*, **39**, 2434 (2000a).
- Matsufuji, T., Nakagawa, S., Nishiyama, N., Matsukata, M. and Ueyama, K., "Synthesis and Permeation Studies of Ferrierite/Alumina Composite Membranes," *Micropor. Mesopor. Mater.*, **38**, 43 (2000b).
- Millot, B., Méthivier, A., Jobic, H., Moueddeb, H. and Dalmon, J.-A., "Permeation of Linear and Branched Alkanes in ZSM-5 Support Membranes," *Micropor. Mesopor. Mater.*, **38**, 85 (2000).
- Nelson, P. H., Tsapatsis, M. and Auerbach, S. M., "Modeling Permeation through Anisotropic Zeolite Membranes with Nanoscopic Defects," *J. Membr. Sci.*, **184**, 245 (2001).
- Nikolakis, V., Xomeritakis, G., Abibi, A., Dickson, M., Tsapatsis, M. and Vlachos, D. G., "Growth of a Faujasite Zeolite Membrane and its Application in the Separation of Saturated/Unsaturated Hydrocarbon Mixtures," *J. Membr. Sci.*, **184**, 209 (2001).
- Nishiyama, N., Park, D. H., Koide, A., Egashira, Y. and Ueyama, K., "A Mesoporous Silica (MCM-48) Membrane: Preparation and Characterization," *J. Membr. Sci.*, **182**, 235 (2001).
- Noack, M., Köisch, P., Caro, J., Schneider, M., Toussaint, P. and Sieber, I., "MFI Membranes of Different Si/Al Ratios for Pervaporation and Steam Permeation," *Micropor. Mesopor. Mater.*, **35-36**, 253 (2000).
- Okamoto, K.-I., Kita, H., Horii, K., Tanaka, K. and Kondo, M., "Zeolite NaA Membrane: Preparation, Single-Gas Permeation, and Pervaporation and Vapor Permeation of Water/Organic Liquid Mixtures," *Ind. Eng. Chem. Res.*, **40**, 163 (2001).
- Pan, M. and Lin, Y. S., "Template-free Secondary Growth Synthesis of MFI type Zeolite Membranes," *Micropor. Mesopor. Mater.*, **43**, 319 (2001).
- Poshusta, J. C., Tuan, V. A., Pape, E. A., Noble, R. D. and Falconer, J. L., "Separation of Light Gas Mixtures Using SAPO-34 Membranes," *AIChE J.*, **46**, 779 (2000).
- Poshusta, J. C., Noble, R. D. and Falconer, J. L., "Characterization of SAPO-34 Membranes by Water Adsorption," *J. Membr. Sci.*, **186**, 25 (2001).
- Tsai, C.-Y., Tam, S.-T., Lu, Y. and Brinker, C. J., "Dual-layer Asymmetric Microporous Silica Membranes," *J. Membr. Sci.*, **169**, 255 (2000).
- Tuan, V. A., Falconer, J. L. and Noble, R. D., "Isomorphous Substitution of Al, Fe, B, and Ge into MFI-zeolite Membranes," *Micropor. Mesopor. Mater.*, **41**, 269 (2000).
- Van de Graaf, J. M., Kapteijn, F. and Moulijn, J. A., "Diffusivities of Light Alkanes in a Silicalite-1 Membrane Layer," *Micropor. Mesopor. Mater.*, **35-36**, 267 (2000).
- Watanabe, H., "CO₂ Removal from Synthetic Natural Gas for City Gas Use," *J. Membr. Sci.*, **154**, 121 (1999).
- Xomeritakis, G., Nair, S. and Tsapatsis, M., "Transport Properties of Alumina-supported MFI Membranes Made by Secondary (seeded) Growth," *Micropor. Mesopor. Mater.*, **38**, 61 (2000).
- Xu, X., Yang, W., Liu, J., Chen, X., Lin, L., Stroh, N. and Brunner, H., "Synthesis and Gas Permeation Properties of an NaA Zeolite Membrane," *Chem. Commun.*, 603 (2000).