

## The Effect of HCl and H<sub>2</sub>O on the H<sub>2</sub>S Removing Capacities of Zn-Ti-based Desulfurization Sorbents Promoted by Cobalt and Nickel Oxide

Hee Kwon Jun, Suk Yong Jung, Tae Jin Lee\* and Jae Chang Kim<sup>†</sup>

Department of Chemical Engineering, Kyungpook National University, Daegu 702-701, South Korea

\*School of Chemical Engineering and Technology, Yeungnam University, Kyongsan 712-749, South Korea

(Received 9 July 2003 • accepted 6 October 2003)

**Abstract**—The sulfur removing capacities of various Zn-Ti-based sorbents were investigated in the presence of H<sub>2</sub>O and HCl at high-(sulfidation, 650 °C; regeneration, 800 °C) and medium-(sulfidation, 480 °C; regeneration, 580 °C) temperature conditions. The H<sub>2</sub>O effect of all sorbents was not observed at high-temperature conditions. At medium-temperature conditions, the reaction rate of ZT (Zn/Ti : 1.5) sorbent decreased with the level of H<sub>2</sub>O concentration, while modified (ZTC, ZTN) sorbents were not affected by the water vapor. HCl vapor resulted in the deactivation of ZT sorbent with a cycle number at high-temperature due to the production of ZnCl<sub>2</sub> while the sulfur removing capacities of ZTC and ZTN sorbents were maintained during 4-5 cyclic tests. In the case of medium-temperature conditions, ZT sorbent was poisoned by HCl vapor while cobalt and nickel added to ZT sorbent played an important catalytic role to prevent from being poisoned by HCl due to providing heat, emitted when these additives quickly react with H<sub>2</sub>S even at medium-temperature conditions, to the sorbents.

Key words: Desulfurization, Zn-Ti Based Sorbent, HCl and H<sub>2</sub>O

### INTRODUCTION

The integrated gasification combined cycle (IGCC) is considered to be among the most efficient and environmentally acceptable technologies for generating power from coal [Woudstra and Woudstra, 1995]. To use this technology, the removal of pollutants such as H<sub>2</sub>S, NH<sub>3</sub> and HCl from coal-derived fuel gas is needed. Among the pollutants, sulfur, which exists in the form of hydrogen sulfide (H<sub>2</sub>S) under the highly reducing conditions of a gasifier, must be removed from the hot coal gas not only to protect equipment against corrosiveness in the later stages of the process, but also to meet strict government regulations for sulfur emissions. To remove hydrogen sulfide from coal-derived gas, several metal oxide materials have been studied in order to develop regenerable sorbents in high- and medium-temperature ranges under the highly reducing conditions of a gasifier [Gupta et al., 2000; Gupta and O'Brien, 2000; Shemwell et al., 2000, 2001; Lee et al., 1997, 2001; Liu et al., 2000; Slimane and Abbsian, 2000, 2001; Jun et al., 2001, 2002; Siriwardane et al., 2000; Kang et al., 2000; Pineda et al., 2000; Sasaoka et al., 2000, 2001; Hatori et al., 2001; Jothimurugesan and Gangwal, 1998; Kirshnan et al., 1995; Yi et al., 2001; Song et al., 2000]. Nowadays, because of process equipment limitations and other variables such as fuel gas alkali content, the optimum temperature for fuel gas desulfurization within this process is estimated to be from 350-550 °C. The roles of additives and supporters, however, have not been clearly defined in this temperature range because of the lack of identification of new active sites and their mechanisms. In addition, there have been very few reports about the effect of H<sub>2</sub>O and HCl in coal-derived fuel gas in medium temperature conditions. The major objectives of this work are to identify any deleterious

changes in the ZT-based sorbents caused by H<sub>2</sub>O and HCl in the fixed-bed reactor and in particular, the catalytic role of additives such as cobalt and nickel in the high- and medium-temperature conditions.

### MATERIALS AND METHODS

#### 1. Preparation of the Sorbent

The zinc titanate (ZT) and modified (ZTC, ZTN) sorbents used in this study were prepared by physical mixing. Zinc oxide, titanium dioxide and cobalt or nickel oxide, of which the particle size was about 200-300 mesh, were sufficiently mixed with an inorganic binder, bentonite, for 1-2 h. Next an organic binder, ethylene glycol (EG), was added to the mixture in order to make a slurry. An extruder was used to formulate pellets with an outer diameter of 1 mm from the slurry. These wet pellets were dried for 4 h in order to remove ethylene glycol from the material in the temperature range of 250-300 °C. The dried pellets were calcined in a muffle furnace for 12 h at 1,000 °C, and then ground to particle size in the range of 250-300 µm in diameter. The ramping rate of the temperature was maintained at 3 °C/min. The mole ratio of Zn to Ti and the amounts of additives added were fixed at 1.5 : 1 and 20 wt%, respectively.

#### 2. Apparatus and Procedure

Multiple cycles of sulfidation/regeneration were performed in a fixed-bed quartz reactor with a diameter of 1 cm placed in an electric furnace. One gram of sorbent was packed into the reactor, and the space velocity (SV) was maintained at 5,000 h<sup>-1</sup> to minimize severe pressure drops and channeling phenomena. All of the volumetric flows of gas were measured at standard temperature and pressure (STP) conditions. The temperature of the inlet and outlet lines of the reactor was maintained above 120 °C to prevent condensation of water vapor produced in the sulfidation processes. The out-

<sup>†</sup>To whom correspondence should be addressed.

E-mail: kjchang@knu.ac.kr

**Table 1. Experimental conditions for Zn-Ti-based sorbents**


	Sulfidation		Regeneration	
Temperature (°C)	480-650		580-800	
Pressure (atm)	1		1	
Flow rate (ml/min)	50		50	
Gas composition (vol%)	H <sub>2</sub> S	1.5	O <sub>2</sub>	3-5
	H <sub>2</sub>	11.7	N <sub>2</sub>	balance
	CO	9.6		
	CO <sub>2</sub>	5.2		
	HCl	0.2		
	H <sub>2</sub> O	5-20		
	N <sub>2</sub>	balance		

let gases from the reactor were automatically analyzed every 8 min by a thermal conductivity detector (TCD) equipped with an auto-sampler (Valco). The column used in the analysis was a 1/8-in. Teflon tube packed with Porapak T. The conditions of sulfidation and regeneration and the composition of mixed gases are shown in Table 1. When the H<sub>2</sub>S concentration of the outlet gases reached 15,000 ppm, the concentration of H<sub>2</sub>S at the inlet stream of mixed gases, an inert nitrogen gas without H<sub>2</sub>S was introduced to purge the system until it reached the regeneration temperature. Finally, nitrogen gas mixed with 3 vol% of oxygen was introduced to regenerate the sulfurized sorbents until the SO<sub>2</sub> concentration reached 200 ppm.

## RESULTS AND DISCUSSION


### 1. H<sub>2</sub>S Performance in the Presence of H<sub>2</sub>O

Fig. 1 shows the sulfur removing capacities of various Zn-Ti-based sorbents under gas compositions with 10 vol% H<sub>2</sub>O at high-temperature conditions. The X-axis indicates the cyclic number considering sulfidation/regeneration reaction as 1 cycle, and the Y-axis indicates the amount of the sulfur absorbed per 1 g sorbent until H<sub>2</sub>S concentration emitted from the reactor reached 200 ppm. The sulfur removing capacities of all the sorbents showed about 16-24 g S/g sorbent at the initial cyclic number. These sulfur removing capacities were almost completely consistent with the theoretical values of the sorbents, indicating that the slope of the H<sub>2</sub>S breakthrough

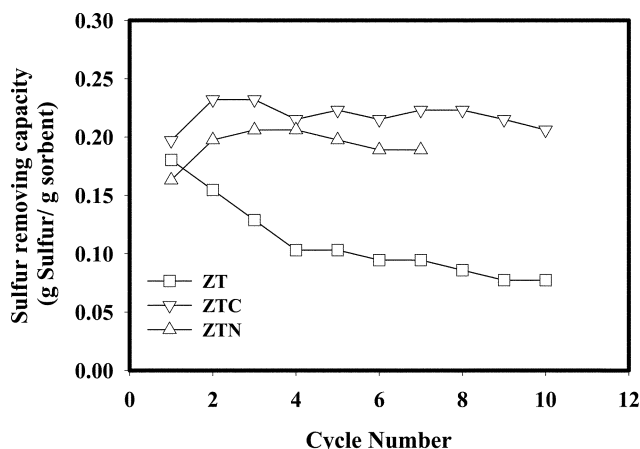

**Fig. 1.** Sulfur removing capacities of various Zn-Ti-based sorbents under gas compositions with 10 vol% H<sub>2</sub>O at 650 °C.

curves suddenly increased at the H<sub>2</sub>S breakthrough point and most of the metal oxides besides TiO<sub>2</sub>, found as a non-active component for H<sub>2</sub>S removal in a previous paper [Jun et al., 2001, 2002], participated in H<sub>2</sub>S absorption before reaching the breakthrough point. From the results of an experiment, in which the capacities were tested in the gas composition without H<sub>2</sub>O vapor, it was observed that the sulfur removing capacities of the Zn-Ti-based sorbents were not affected by water vapor at high-temperature conditions. Deactivation of sulfur removing capacity for the ZT sorbent with the cyclic number, unlike ZTC and ZTN, can be explained by the change of physical properties of the ZT sorbent as reported in a previous paper [Kang et al., 2002]. Fig. 2 shows the sulfur removing capacities of various Zn-Ti-based sorbent under gas compositions with/without 10 vol% H<sub>2</sub>O at medium-temperature conditions. Most of the sorbents showed lower sulfur removing capacities compared with the results at high-temperature conditions. The sulfur removing capacities of ZT sorbent in the absence of H<sub>2</sub>O decreased with the cyclic number, while those of the ZTC and ZTN sorbent maintained initial values even at over 10 cycles. In the case of gas composition with 10 vol% H<sub>2</sub>O, the sulfur removing capacities of the ZTC and ZTN sorbent did not depend on water vapor while the ZT sorbent showed the sulfur removing capacity less than 5 g S/g sorbent at every cycle. To explain the deactivation of the ZT sorbent in the presence of H<sub>2</sub>O, the H<sub>2</sub>S breakthrough curves of the ZT sorbent were

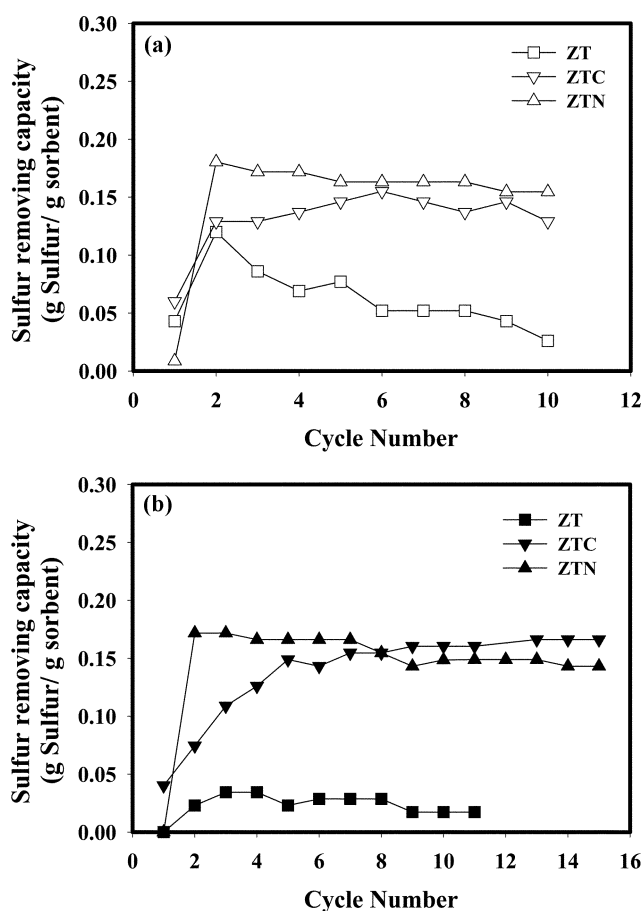

**Fig. 2.** Sulfur removing capacities of various Zn-Ti-based sorbents under gas compositions with/without 10 vol% H<sub>2</sub>O at 480 °C; (a) in the absence of H<sub>2</sub>O, (b) in the presence of H<sub>2</sub>O.

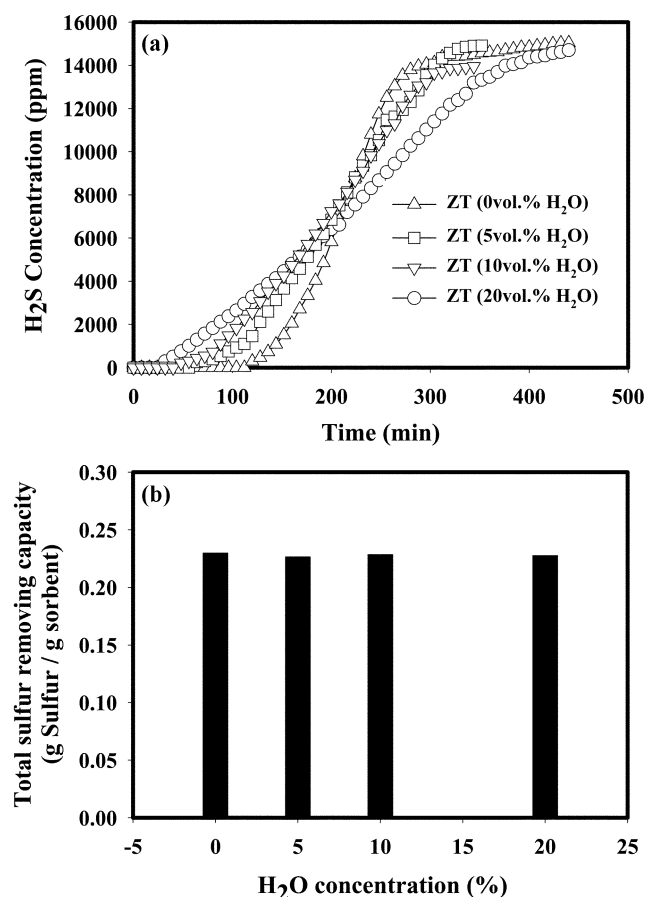


Fig. 3. Breakthrough curves (a) and total sulfur removing capacities, (b) of ZT sorbent with H<sub>2</sub>O concentration at 480 °C.

investigated with the H<sub>2</sub>O concentration and shown in Fig. 3(a). It was shown that the slope of the breakthrough curve gradually decreased with the H<sub>2</sub>O concentration. In addition, the total sulfur removing capacities of the ZT sorbent, the amount of sulfur absorbed until the output concentration reached the input value of the reactor, were calculated from these breakthrough curves and are shown in Fig. 3(b). The total sulfur removing capacities of the ZT sorbent showed 24 g S/g sorbent regardless of the H<sub>2</sub>O concentrations. Considering that the theoretical value of the ZT sorbent was about 24 g S/g sorbent, these results indicate that water vapor resulted in the reduction of the reaction rate between zinc oxide, major active sites for H<sub>2</sub>S absorption, and H<sub>2</sub>S at medium-temperature conditions.

## 2. H<sub>2</sub>S Performance in the Presence of HCl

To identify the HCl effect of the Zn-Ti-based desulfurization sorbents, their sulfur removing capacities were investigated in the presence of 5 vol% H<sub>2</sub>O and 0.2 vol% HCl at high- and medium-temperature conditions. An aqueous solution with 20% HCl was used, and the concentration of H<sub>2</sub>O and HCl was controlled by their relative vapor pressures. Fig. 4(a) shows the sulfur removing capacities of various sorbents with the cyclic number under gas composition with HCl and H<sub>2</sub>O at high-temperature conditions. The sulfur removing capacity of all the sorbents was slightly increased compared with the results obtained at gas composition without H<sub>2</sub>O and HCl. Fig. 4(b) shows the total sulfur removing capacities of various sorbents with the same experimental condition. The total sulfur

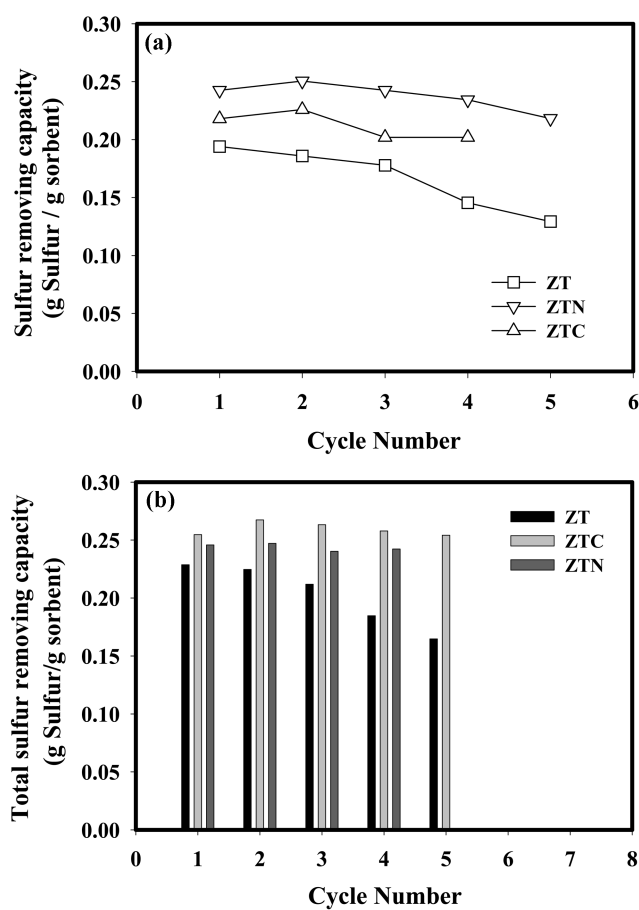


Fig. 4. Sulfur removing capacities (a) and total sulfur removing capacities, (b) of various Zn-Ti-based sorbents under gas composition with 5 vol% H<sub>2</sub>O and 0.2 vol% HCl at 650 °C.

removing capacities of the ZT sorbent gradually decreased with the cyclic number, while those of the ZTC and ZTN sorbent did not change. The deactivation of the ZT sorbent, as other researchers mentioned [Gupta and O'Brien, 2000], can be explained by the vaporization of ZnCl<sub>2</sub> formed by the side reaction between ZnO and HCl and reported as a liquid phase in the range of 283 °C to 732 °C. In the case of ZTC and ZTN sorbents, it was thought that the cobalt and nickel chloride formed by the side reaction with HCl were not a liquid phase at our experimental conditions and that they were transformed to their sulfides through reaction with H<sub>2</sub>S without vaporization. In addition, it is clear the cobalt and nickel intercalated within the lattices of spinel structure such as Zn<sub>1-x</sub>Ti<sub>x</sub>O<sub>4</sub> played an important role in preventing the deactivation of Zn-based sorbent. Fig. 5(a) shows the sulfur removing capacities of various sorbents with the cyclic number under gas composition with HCl and H<sub>2</sub>O at medium-temperature conditions. The sulfur removing capacity of the ZT sorbent showed about 5 g S/g sorbent at the initial period and this value was maintained until four cycles. In addition, as shown in Fig. 5(b), its total sulfur removing capacity was about 6 g S/g sorbent, regardless of the cyclic number. From these results, it was thought that HCl could adsorb on the zinc oxide, active site, and prevent zinc oxide from reacting with H<sub>2</sub>S at medium-temperature conditions. The existence of chloride within the spent ZT sorbent was confirmed by using ion chromatography after sulfidation.

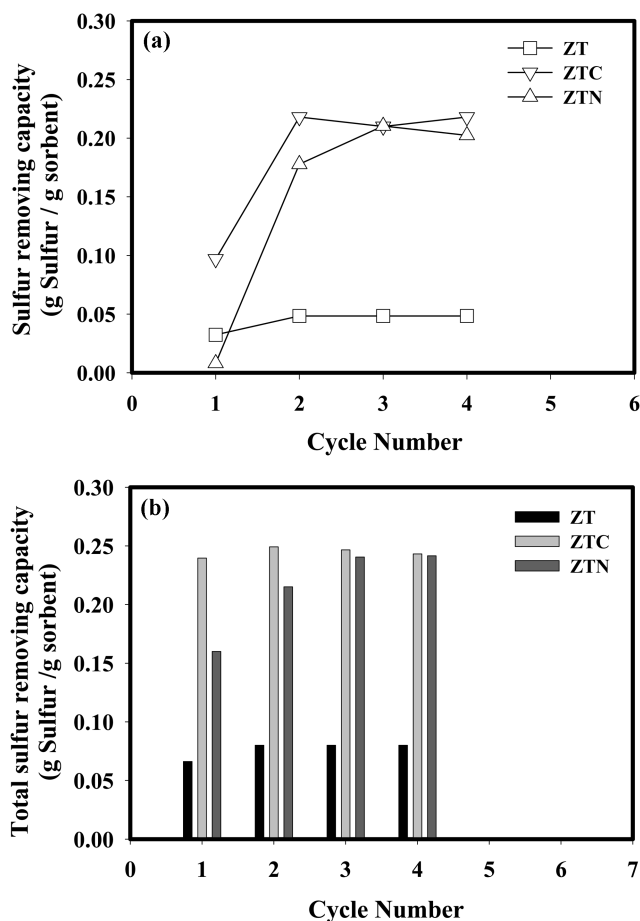


Fig. 5. Sulfur removing capacities (a) and total sulfur removing capacities, (b) of various Zn-Ti-based sorbents under gas composition with 5 vol%  $\text{H}_2\text{O}$  and 0.2 vol%  $\text{HCl}$  at  $480^\circ\text{C}$ .

The sulfur removing capacities of the ZTC and ZTN sorbent were maintained nearly 20 g S/g sorbent without deactivation after two cycles and these values were 6 g S/g sorbent higher than those obtained at gas composition without  $\text{HCl}$  and  $\text{H}_2\text{O}$ . Considering that the total sulfur removing capacities, as shown in Fig. 5(b), were not changed (about 23–24 g S/g sorbent) by addition of  $\text{HCl}$  and  $\text{H}_2\text{O}$ . These results indicate that the slope of the breakthrough curve increased at gas composition with  $\text{HCl}$ , which can be explained by the increase of the reaction rate between the ZTC, ZTN sorbents and  $\text{H}_2\text{S}$ . Also, as mentioned in the previous section, the sulfur removing capacities of the ZTC and ZTN sorbent did not depend on the amount of  $\text{H}_2\text{O}$  even at medium-temperature conditions; the increase of the reaction rate can be related with the presence of  $\text{HCl}$  and can be explained from the following section.

### 3. The Heat Effect of Sorbent

To investigate the role of cobalt and nickel added to the ZT sorbent, the temperature change of the reactor in which sorbents were packed was measured during sulfidation in gas composition without  $\text{H}_2\text{O}$  at medium-temperature conditions. As shown in Fig. 6(a), the temperature change of the ZT sorbent was not observed, while the temperature of the reactor in which the ZTC and ZTN sorbent was packed increased 7–10  $^\circ\text{C}$  at the initial period and this gradually decreased with the reaction time until sulfidation temperature.

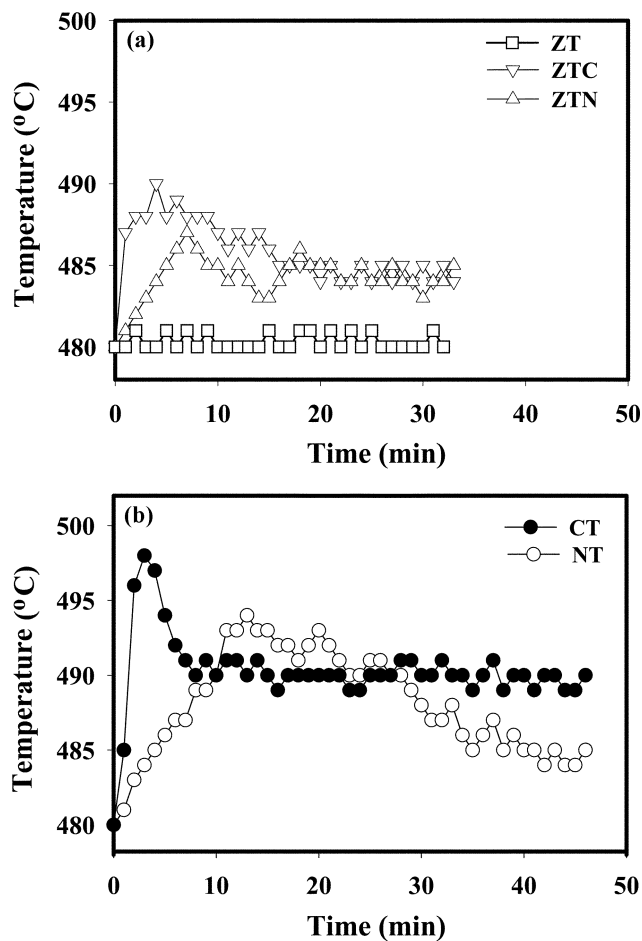


Fig. 6. The change of reactor temperature during sulfidation at  $480^\circ\text{C}$ ; (a) various Zn-Ti-based sorbents, (b) CT, NT sorbents without zinc.

In addition, the CT and NT sorbents were prepared by mixing additives such as cobalt and nickel oxides with  $\text{TiO}_2$ , respectively. The amount of additives added to the  $\text{TiO}_2$  was the same as that of  $\text{ZnO}$  added to the  $\text{TiO}_2$ . As shown in Fig. 6(b), the reactor temperature individually increased 18  $^\circ\text{C}$  for CT and 13  $^\circ\text{C}$  for NT in the initial period and gradually decreased with the reaction time. The reason why the reactor temperature of the ZT sorbent did not change during sulfidation was thought to be that the reaction rate between the zinc oxide and  $\text{H}_2\text{S}$  was too slow in order to measure the temperature change in our experimental conditions. In the case of the ZTC and ZTN sorbent, however, their temperature change during sulfidation can explain that the reaction rates between the additives and  $\text{H}_2\text{S}$  are so fast even at medium-temperature conditions. This heat effect, as reported in previous papers [Jun et al., 2001, 2002], was also observed in ZTC sorbent during regeneration. The temperature of ZTC sorbent increased (about 10  $^\circ\text{C}$ ) during regeneration by using 3% oxygen. It was found that this heat emitted when cobalt sulfides were regenerated to their oxides improved the regeneration of zinc sulfides even at low temperature due to the catalytic role of cobalt additive. If the additives, cobalt and nickel, quickly react with  $\text{H}_2\text{S}$  during sulfidation even at medium-temperature conditions and this reaction can emit absorption heat, this heat can prevent the reaction rate between  $\text{ZnO}$  and  $\text{H}_2\text{S}$  from reducing under gas composi-

tion with H<sub>2</sub>O and prevents HCl from poisoning the active site such as ZnO at medium-temperature conditions. In addition, this heat can improve the reaction rate between ZnO and HCl as well as between ZnO and H<sub>2</sub>S at medium-temperature condition. If ZnO within the ZTC and ZTN sorbent reacts with HCl and transforms to ZnCl<sub>2</sub>, it is the liquid phase in the temperature range of 283 °C to 732 °C and it is more accessible for reactions with H<sub>2</sub>S than the solid phase ZnO [Gupta and O'Brien, 2000]. This mechanism, therefore, explains the enhancement in the sulfur removing capacity of the sorbent in the presence of HCl, as shown in Fig. 4(a) and Fig. 5(a).

## CONCLUSIONS

The sulfur removing capacities of various Zn-Ti-based sorbents were investigated in the presence of H<sub>2</sub>O and HCl at high- and medium-temperature conditions. The H<sub>2</sub>O effect of all the sorbents was not observed at high-temperature conditions. At medium-temperature conditions, the reaction rate of the ZT sorbent decreased with H<sub>2</sub>O concentration, while the ZTC and ZTN sorbent were not affected by the water vapor. The presence of HCl resulted in the deactivation of the ZT sorbent with the cycle number at high-temperature conditions due to the production of ZnCl<sub>2</sub> while the sulfur removing capacity of the ZTC and ZTN sorbent was maintained during 4-5 cyclic tests. In the case of medium-temperature conditions, the ZT sorbent showed very low sulfur removing capacity while that of ZTC and ZTN increased 6% compared with the results obtained at gas composition without HCl. From these results, it was concluded that cobalt and nickel added to the ZT sorbent played an important catalytic role in preventing the reaction rate of the Zn-Ti-based sorbent from reducing in the presence of H<sub>2</sub>O and preventing HCl from poisoning the active site for H<sub>2</sub>S removal in the presence of HCl due to providing heat, emitted when these additives quickly reacted with H<sub>2</sub>S even at medium-temperature conditions, to the sorbents.

## REFERENCES

- Gupta, R. P. and O'Brien, W. S., "Desulfurization of Hot Syngas Containing Hydrogen Chloride Vapors Using Zinc Titanate Sorbents," *Ind. Eng. Chem. Res.*, **39**, 610 (2000).
- Gupta, R. P., Turk, B. S., Merkel, T. C., Krishnan, G. N. and Cicero, D. C., "Gaseous Contaminant Control for IGCC Application," 17<sup>th</sup> Annual Pittsburgh Coal Conference, September (2000).
- Hatori, M., Sasaoka, E. and Uddin, Md. A., "Role of H<sub>2</sub>O in Oxidative Regeneration of ZnS From High-Temperature Desulfurization ZnO Sorbent," *Ind. Eng. Chem. Res.*, **40**, 1884 (2001).
- Jothimurugesan, K. and Gangwal, S. K., "Regeneration of Zinc Titanate H<sub>2</sub>S Sorbents," *Ind. Eng. Chem. Res.*, **37**, 1929 (1998).
- Jun, H. K., Lee, T. J. and Kim, J. C., "Role of Iron Oxide in the Promotion Zn-Ti-Based Desulfurization Sorbents during Regeneration at Middle Temperatures," *Ind. Eng. Chem. Res.*, **41**, 4733 (2002).
- Jun, H. K., Lee, T. J., Ryu, S. O. and Kim, J. C., "A Study of Zn-Ti-Based H<sub>2</sub>S Removal Sorbents Promoted with Cobalt Oxides," *Ind. Eng. Chem. Res.*, **40**, 3547 (2001).
- Kang, S. C., Jun, H. K., Lee, T. J., Ryu, S. O. and Kim, J. C., "The Characterization of Zn-based Desulfurization Sorbents on Various Supports," *HWAHAK KONGHAK*, **40**, 289 (2002).
- Krishnan, G. N., Gupta, R. P. and Ayala, R., "Development of Disposable Sorbents for Chloride Removal from High-Temperature Coal-Derived Gases," Proceeding of the Advanced Coal-Fired Power Systems '95 Review Meeting Volume II, 613 (1995).
- Lee, H. S., Kang, M. P., Song, Y. S., Lee, T. J. and Rhee, Y. W., "Desulfurization Characteristics of CuO-Fe<sub>2</sub>O<sub>3</sub> Sorbents," *Korean J. Chem. Eng.*, **18**, 635 (2001).
- Lee, T. J., Kwon, W. T., Chang, W. C. and Kim, J. C., "A Study on Regeneration of Zinc Titanate Sorbents for H<sub>2</sub>S Removal," *Korean J. Chem. Eng.*, **14**, 513 (1997).
- Liu, K., Xie, W., Li, D., Pan, W. P., Riley, J. T. and Riga, A., "The Effect of Chlorine and Sulfur on the Composition of Ash Deposits in a Fluidized Bed Combustion System," *Energy & Fuels*, **14**, 963 (2000).
- Pineda, M., Palacios, J. M., Alonso, L., Garcia, E. and Moliner, R., "Performance of Zinc Oxide Based Sorbents for Hot Coal Gas Desulfurization in Multicycle Tests in a Fixed-bed Reactor," *Fuel*, **79**, 885 (2000).
- Sasaoka, E., Hatori, M., Sada, N. and Uddin, Md. A., "Role of TiO<sub>2</sub> on Oxidative Regeneration of Spent High-Temperature Desulfurization Sorbent ZnO-TiO<sub>2</sub>," *Ind. Eng. Chem. Res.*, **39**, 3844 (2000).
- Sasaoka, E., Hatori, M., Yoshimur, H., Su, C. and Uddin, Md. A., "Role of H<sub>2</sub>O in Oxidation of Spent High-temperature Desulfurization Sorbent Fe<sub>2</sub>O<sub>3</sub> and CuO in the Presence of O<sub>2</sub>," *Ind. Eng. Chem. Res.*, **40**, 2512 (2001).
- Shemwell, B., Atal, A., Levendis, Y. A. and Simons, G. A., "A Laboratory Investigation on Combined In-Furnace Sorbent Injection and Hot Flue-Gas Filtration to Simultaneously Capture SO<sub>2</sub>, NO<sub>x</sub>, HCl, and Particulate Emissions," *Environ. Sci. Technol.*, **34**, 4855 (2000).
- Shemwell, B., Levendis, Y. A. and Simons, G. A., "Laboratory Study on the High-Temperature Capture of HCl Gas by Dry-Injection of Calcium-based Sorbents," *Chemosphere*, **42**, 785 (2001).
- Siriwardane, R. V., Gardner, T., Poston, J. A. Jr. and Fisher, E. P., "Spectroscopic Characterization of Nickel Containing Desulfurization Sorbents," *Ind. Eng. Chem. Res.*, **39**, 1106 (2000).
- Slimane, R. B. and Abbasian, J., "Regenerable Mixed Metal Oxide Sorbents for Coal Gas Desulfurization at Moderate Temperatures," *Advances in Environmental Research*, **4**, 147 (2000).
- Slimane, R. B. and Abbasian, J., "Utilization of Metal Oxide-Containing Waste Materials for Hot Coal Gas Desulfurization," *Fuel Processing Technology*, **70**, 97 (2001).
- Song, Y. K., Lee, K. B., Lee, H. S. and Rhee, Y. W., "Reactivity of Copper Oxide-Based Sorbent in Coal Gas Desulfurization," *Korean J. Chem. Eng.*, **17**, 691 (2000).
- Woudstra, T. and Woudstra, N., "Energy Analysis of Hot-gas Clean up in IGCC System," *J. Inst. Energy*, **68**, 157 (1995).
- Yi, C. K., Jo, S. H., Lee, B. H., Lee, S. Y., Son, J. E. and Jin, G. T., "Simultaneous Experiments of Sulfidation and Regeneration in Two Pressurized Fluidized-bed Reactors for Hot Gas Desulfurization of IGCC," *Korean J. Chem. Eng.*, **18**, 1005 (2001).