

## Cloud-point measurement of the biodegradable poly(d,l-lactide-co-glycolide) solution in supercritical fluid solvents

Hun-Soo Byun<sup>†</sup> and Ha-Yeon Lee

Department of Chemical System Engineering, Chonnam National University, Yeosu, Jeonnam 550-749, Korea  
(Received 20 April 2006 • accepted 19 June 2006)

**Abstract**—Experimental data of high pressure phase behavior between 35 °C and 105 °C and pressures up to 2,200 bar is presented for poly(d,l-lactic acid)(d,l-PLA) and poly(lactide-co-glycolide)<sub>15</sub> (PLGA<sub>15</sub>), PLGA<sub>25</sub>, and PLGA<sub>50</sub> in supercritical carbon dioxide, trifluoromethane (CHF<sub>3</sub>), chlorodifluoromethane (CHClF<sub>2</sub>), dichloromethane (CH<sub>2</sub>Cl<sub>2</sub>), and chloroform (CHCl<sub>3</sub>). d,l-PLA dissolves in carbon dioxide at pressures of 1,250 bar, in CHF<sub>3</sub> at pressures of 500 to 750 bar, and in CHClF<sub>2</sub> at pressures of 30–145 bar. As glycolic acid (glycolide) is added to the backbone of PLGA, the cloud point pressure increases by 36 bar/(mol GA) in carbon dioxide, 27 bar/(mol GA) in CHF<sub>3</sub>, and by only 3.9 bar/(mol GA) in CHClF<sub>2</sub>. PLGA<sub>50</sub> does not dissolve in carbon dioxide at pressures of 2,800 bar, whereas it is readily soluble in CHClF<sub>2</sub> at pressures as low as 95 bar at 40 °C. Cloud point behavior of d,l-PLA, PLGA<sub>15</sub>, and PLGA<sub>25</sub> in supercritical carbon dioxide shows the effect of glycolide content between 35 °C and 108 °C. Also, the phase behavior for poly(lactic acid) - carbon dioxide-CHClF<sub>2</sub> mixture shows the changes of pressure-temperature slope, and with CHClF<sub>2</sub> concentration of 6 wt%, 19 wt%, 36 wt% and 65 wt%. The cloud-point behavior shows the impact of glycolide content on the phase behavior of PLA, PLGA<sub>15</sub>, PLGA<sub>25</sub> and PLGA<sub>50</sub> in supercritical CHClF<sub>2</sub>. A comparison was made between the phase behaviors of d,l-PLA and poly(l-lactide)(l-PLA) in supercritical CHF<sub>3</sub>. The phase behavior of CHF<sub>3</sub> as a cosolvent for 5 wt% d,l-PLA-supercritical carbon dioxide system is presented for the effect being added 10 wt% and 29 wt% to CHF<sub>3</sub> content.

**Key words:** Poly(l-lactide), Poly(lactide-co-glycolide), Cloud Point Data, Supercritical CO<sub>2</sub>, CHClF<sub>2</sub>, CHF<sub>3</sub>, Phase Behavior, CHCl<sub>3</sub>, CH<sub>2</sub>Cl<sub>2</sub>

### INTRODUCTION

Supercritical fluids are an attractive alternative to incompressible liquid solvents, since they can have liquid-like dissolving power while exhibiting the transport properties of a gas. They have been used in a variety of polymer processes such as polymerization process, extraction, separation, and industrial application [McHugh and Krukoni, 1994; Benedetti et al., 1997; Lee, 2003; Lee et al., 2006].

Poly(d,l-lactide-co-glycolide) (PLGA) has been utilized in the medical industry such as in biodegradable sutures [Middleton and Tipton, 1998; Park et al., 2004]. PLGA has been tested for numerous biological applications including polymeric drug delivery devices, synthetic bone scaffolding and dental prosthetic devices [Mandel and Wang, 1999; Kim et al., 1996; Bodmeier et al., 1995]. Since PLGA is used in biological applications, the solvents used to process these copolymers should be pharmacologically acceptable. Recently, supercritical CO<sub>2</sub> has been investigated as a viable solvent for processing PLGA copolymers. To thermodynamic knowledge, the phase behavior of PLGA copolymers in CO<sub>2</sub> has been reported [Kuk et al., 2002; Conway et al., 2001]. Kuk et al. have performed experimental phase behavior studies for poly(d,l-lactide)-HFC-22, HFC-23 and HFC-32 system at temperature 40 °C to 100 °C using a high pressure equilibrium apparatus equipped with a variable volume view cell. The phase behavior experimental data for poly(lac-


tide-co-glycolide) solution in supercritical CO<sub>2</sub>, CHF<sub>3</sub> and CHClF<sub>2</sub> were reported by Conway et al. [2001]. Conway et al. studied the phase behavior and mixture density data between 20 and 100 °C and pressures to 3,000 bar.

The purpose of this work is to present the determination of the impact of glycolic acid content in PLGA on the temperatures and pressures. We measured the cloud-point of l-PLA, d,l-PLA, PLGA<sub>15</sub>, PLGA<sub>25</sub> and PLGA<sub>50</sub> in solvent mixtures of compressed liquid (CHCl<sub>3</sub> and CH<sub>2</sub>Cl<sub>2</sub>) and supercritical CO<sub>2</sub>, CHF<sub>3</sub> and CHClF<sub>2</sub>. The cloud-point behavior measuring technique has been used to determine the location of the phase boundary between fluid (single) phase and two-phase regions [Kirby and McHugh, 1999]. We measured the phase behavior by using a high pressure phase equilibria apparatus with a variable-volume view cell. The cloud-point pressures of the biodegradable polymers in supercritical CO<sub>2</sub>, CHF<sub>3</sub> and CHClF<sub>2</sub> were characterized as functions of pressure, temperature and glycolide concentration. The cloud-point data presented in this work would be useful for establishing operating conditions in the biopolymer particle formation using supercritical fluid solvent processing.

### EXPERIMENTAL SECTION

Fig. 1 shows a schematic diagram of the experimental high-pressure apparatus. A detailed description of the experimental apparatus and procedure is given in the previous paper reported [Byun and McHugh, 2000]. The high-pressure variable-volume view cell used in this study is to obtain phase behavior data. The main body

<sup>†</sup>To whom correspondence should be addressed.  
E-mail: hsbyun@chonnam.ac.kr

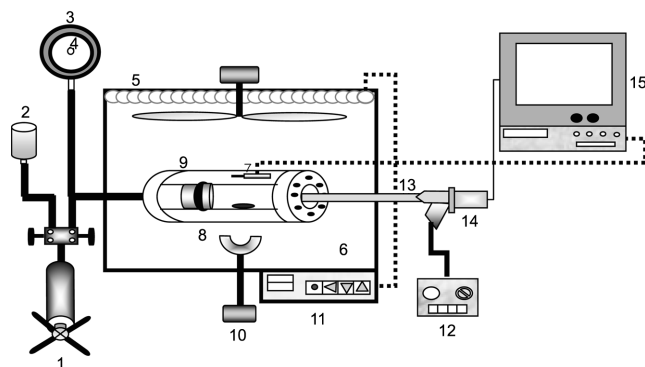

**Fig. 1. Schematic diagram of the experimental high-pressure apparatus for biopolymer-supercritical fluid solvents mixture.**

- |                          |                      |
|--------------------------|----------------------|
| 1. Pressure generator    | 9. Variable cell     |
| 2. Water                 | 10. Motor            |
| 3. Pressure gauge        | 11. Temp. controller |
| 4. Fan                   | 12. Light source     |
| 5. Heater                | 13. Borescope        |
| 6. Air bath              | 14. Camera           |
| 7. Temperature indicator | 15. TV monitor       |
| 8. Magnetic stirrer      |                      |

of the variable-volume cell apparatus is a high nickel content steel (7.0 cm O.D. and 1.59 cm I.D.) with  $\sim 28 \text{ cm}^3$  working volume. A sapphire window (1.9 cm O.D.  $\times$  1.9 cm thick) is fitted to one end of the cell so that the cloud point can be determined visually. The view cell is compressed to the desired operating pressure by displacing a movable piston fitted within the cell using water pressurized with a high-pressure generator (HIP, Inc., Model 37-5.75-60). The system pressure is measured on the water side of the piston with a Heise gauge (Dresser Ind., model CM-108952, 0-3450 bar, accurate to within  $\pm 3.5$  bar). A small correction of one bar is added to the pressure to compensate for the pressure needed to move the piston. The temperature of the view cell is measured to within  $\pm 0.2^\circ\text{C}$  with a platinum-resistance thermometer (Thermometrics Corp., Class A) and connected to a digital multimeter (Yokogawa, model 7563, accurate to within  $\pm 0.005\%$ ). The mixture inside the cell is viewed on a video monitor using a CCD camera (Watec Co., model WAT-202B) coupled to a borescope (Olympus Corp., model F100-038-000-50) placed against the outside of the sapphire window. Light is transmitted into the cell with a fiber optic cable connected at one end to a high-density illuminator (Olympus Optical Co., model ILK-5) and at the other end to the borescope.

While being maintained at room temperature, the cell is purged first with nitrogen at pressures of 3 to 5 bar and then with the  $\text{CO}_2$  solvent at 3 to 6 bar to remove any entrapped air and organic matter. Approximately 1.0 to  $8.0 \pm 0.004 \text{ g}$  of  $\text{CO}_2$  are transferred into the cell, which had been previously loaded with 0.1 to  $7.0 \pm 0.002 \text{ g}$  of polymer and copolymer, depending on the desired about 5 wt% polymer or copolymer in solution.

Cloud points are measured for binary and ternary solutions with a fixed biodegradable copolymer or polymer concentration of  $\sim 5 \text{ wt\%}$ . Cloud points are measured and reproduced at least twice to within  $\pm 2.8 \text{ bar}$  and  $\pm 0.2^\circ\text{C}$ . The cloud point pressure is defined as the point at which the solution becomes so opaque that it is no longer possible to see the stir bar in the mixture.

## 1. Materials

November, 2006

**Table 1. The properties of PLGA copolymers and d,l-PLA polymer used in this work**

Polymers	i.v.*	$M_w$	$M_w/M_n$	$T_g$ ( $^\circ\text{C}$ )
d,l-PLA	0.35-0.45	20,000-30,000	1.8	55
PLGA <sub>15</sub>	0.50-0.65	$\sim 20,000$	1.8	50-55
PLGA <sub>25</sub>	0.50-0.65	$\sim 20,000$	1.8	50-55
PLGA <sub>50</sub>	0.50-0.65	$\sim 12,000$ -16,000	1.8	45-50

\*i.v. is an inherent viscosity (dl/g)

The biodegradable polymers used in this study were obtained from Polysciences, Inc. (Cincinnati, OH). The detailed content of polymer and copolymers presented the Table 1. The poly(l-lactic acid) [l-PLA;  $M_w=200,000$ ] was obtained from Honam Petroleum Chemical Co.

$\text{CHF}_3$  (98% minimum purity),  $\text{CHCl}_3$  (99.9% purity, HPLC grade) and  $\text{CH}_2\text{Cl}_2$  (99.9% purity, HPLC grade) was obtained from Aldrich Chemical Company.  $\text{CO}_2$  (99.9% minimum purity) was obtained from Daesung Industrial Gases Co., and  $\text{CHClF}_2$  (99.8% minimum purity) from Dongil Gas (Yeosu, Korea). All of the solvents and biodegradable polymers were used as received without further purification.

## RESULTS AND DISCUSSION

Table 2 shows the physicochemical properties of  $\text{CO}_2$ ,  $\text{CHF}_3$ ,  $\text{CHClF}_2$ ,  $\text{CHCl}_3$  and  $\text{CH}_2\text{Cl}_2$  [Reid et al., 1987; Daubert and Danner, 1989; Prausnitz et al., 1986; Meyer et al., 1980; Benson et al., 1969]. Notice that the polarizability of  $\text{CO}_2$  and  $\text{CHF}_3$  is identical, which implies that the impact of the quadrupole moment of  $\text{CO}_2$  can be contrasted to the impact of the dipole moment of  $\text{CHF}_3$  on the phase behavior. The dipole moments of  $\text{CHF}_3$  and  $\text{CHClF}_2$  are 1.6 and 1.5 Debye, respectively, and the cloud-point behavior of the d,l-PLA in  $\text{CHF}_3$  and  $\text{CHClF}_2$  can be compared to determine the impact of polarizability on the phase behavior. Also, the dipole moments of  $\text{CHCl}_3$  and  $\text{CH}_2\text{Cl}_2$  show a big difference (1.1 and 1.8 Debye). We compared the phase behaviors of PLGA<sub>15</sub> in different supercritical  $\text{CHCl}_3$  and  $\text{CH}_2\text{Cl}_2$ .

Fig. 2 shows the impact of glycolic acid content on phase behavior of d,l-PLA, PLGA<sub>15</sub> and PLGA<sub>25</sub> in supercritical  $\text{CO}_2$ . The phase behavior for PLGA<sub>15</sub>- $\text{CO}_2$  and PLGA<sub>25</sub>- $\text{CO}_2$  system exhibits UCST region curve with negative slope in  $-0.6 \text{ bar}/^\circ\text{C}$  (PLGA<sub>15</sub>) and  $-2.6 \text{ bar}/^\circ\text{C}$  (PLGA<sub>25</sub>), respectively. The cloud-point curve for d,l-PLA-supercritical  $\text{CO}_2$  system exhibits an LCST curve with positive slope in  $1.4 \text{ bar}/^\circ\text{C}$  (d,l-PLA). The switch from a positive to a negative

**Table 2. Critical temperature  $T_c$ , critical pressure  $P_c$ , polarizability  $\alpha$ , and dipole moment  $\mu$  of the five solvents used in this study**

Solvents	$T_c$ ( $^\circ\text{C}$ )	$P_c$ (bar)	$\alpha$ ( $\text{cm}^3 \times 10^{25}$ )	$\mu$ (Debye)
$\text{CO}_2$	31.0	73.8	26.5	0.0
$\text{CHF}_3$	26.2	48.6	26.5	1.6
$\text{CHClF}_2$	96.2	49.7	44.4	1.5
$\text{CHCl}_3$	263.25	53.7	82.6	1.1
$\text{CH}_2\text{Cl}_2$	236.85	63.0	64.8	1.8

$\text{CO}_2$  possesses a quadrupole moment of  $-4.3 \times 10^{-26} \text{ erg}^{1/2} \text{ cm}^{5/2}$ .

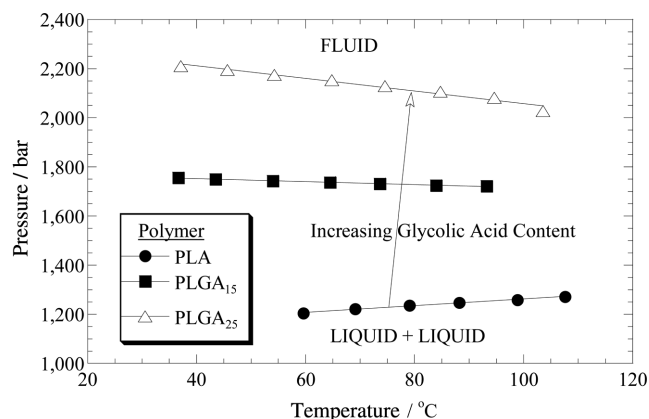


Fig. 2. Impact of glycolic acid (glycolide) content on the phase behavior of PLA, PLGA<sub>15</sub> and PLGA<sub>25</sub> in pure supercritical CO<sub>2</sub>.

slope suggests that the interchange energy, which is a measure of copolymer-CO<sub>2</sub> interactions relative to copolymer-copolymer and CO<sub>2</sub>-CO<sub>2</sub> interactions, is weighted more toward copolymer-copolymer interactions rather than cross-interactions. A cloud point curve with a negative slope also clearly shows that increasing the system pressure, or conversely, does not help in obtaining a single phase as the system temperature is lowered.

It is apparent that the pressures needed to obtain a single phase are fixed more by the glycolic acid content in the backbone of the copolymer rather than the copolymer weight average molecular weight ( $M_w$ ). As shown in Fig. 2, if  $M_w$  governed the location of the cloud point curve, the PLGA<sub>15</sub> and PLGA<sub>25</sub> curves would be at pressures below which needed to dissolve PLA<sub>H</sub> rather than at higher pressures. The PLGA<sub>50</sub> does dissolve in pure CO<sub>2</sub> to a temperature of 120 °C and pressure of 2,800 bar.

Fig. 3 shows the effect of CHClF<sub>2</sub> as a cosolvent for poly(d,l-lactic acid) in supercritical CO<sub>2</sub>. In Fig. 4, the phase behavior of the d,l-PLA-CO<sub>2</sub>-DME mixture was shown. The d,l-PLA-CO<sub>2</sub> mixture was obtained in the range of temperature of 60-107 °C and at pressures of 1,204-1,270 bar, and for d,l-PLA-chlorodifluoromethane (CHClF<sub>2</sub>) mixture at the range of temperature of 65-105 °C and

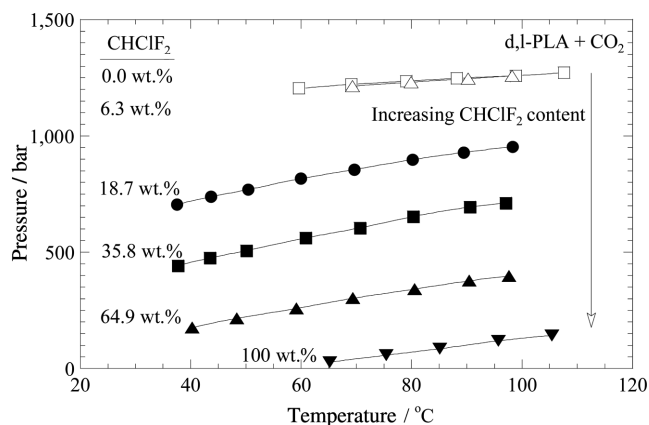


Fig. 3. Effect of CHClF<sub>2</sub> as a cosolvent for poly(d,l-lactic acid) [d,l-PLA] in supercritical CO<sub>2</sub>. The polymer concentration is ~5.0 wt% for each solution.

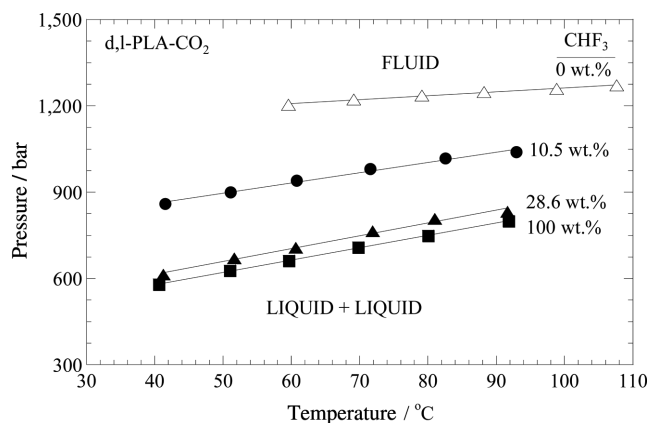


Fig. 4. Effect of CHF<sub>3</sub> as a cosolvent for poly(d,l-lactic acid) in supercritical CO<sub>2</sub>. The polymer concentration is ~5.0 wt% for each solution.

pressures of 28-143 bar. The pressure difference between two systems is due to whether or not a dipole moment in CHClF<sub>2</sub> (1.3 Debye) [Reid et al., 1987] and CO<sub>2</sub> (0.0 Debye) [Reid et al., 1987].

As shown in Fig. 3, the d,l-PLA-CO<sub>2</sub>-6.3 wt% CHClF<sub>2</sub> mixture shows LCST-type behavior of the positive slope, and then the pressure increases slightly at 70-98 °C. With 18.7 wt% CHClF<sub>2</sub> added to the solution, the cloud-point curve exhibits LCST region phase behavior of a positive slope in 4.1 bar/°C. When 35.8 and 64.9 wt% CHClF<sub>2</sub> is added in the d,l-PLA-CO<sub>2</sub> mixture, which shows the LCST-type of the positive slope in 4.6 bar/°C and 3.9 bar/°C, respectively. At 80 °C, the pressure difference of the d,l-PLA-CO<sub>2</sub>-35.8 and 64.9 wt% CHClF<sub>2</sub> system shows about 300 bar, which is caused by the impact of free volume as CHClF<sub>2</sub> concentration increases.

Fig. 4 shows the effect of CHF<sub>3</sub> as a cosolvent for d,l-PLA in supercritical CO<sub>2</sub>. The d,l-PLA-CO<sub>2</sub> mixture was obtained in the range of temperature of 60-108 °C and at pressures of 1,200-1,270 bar, and for d,l-PLA-CHF<sub>3</sub> mixture from 40-90 °C and pressures of 580-800 bar. The pressure difference between two systems is due to whether or not a dipole moment in CHF<sub>3</sub> (1.6 D) and CO<sub>2</sub> (0.0 D),

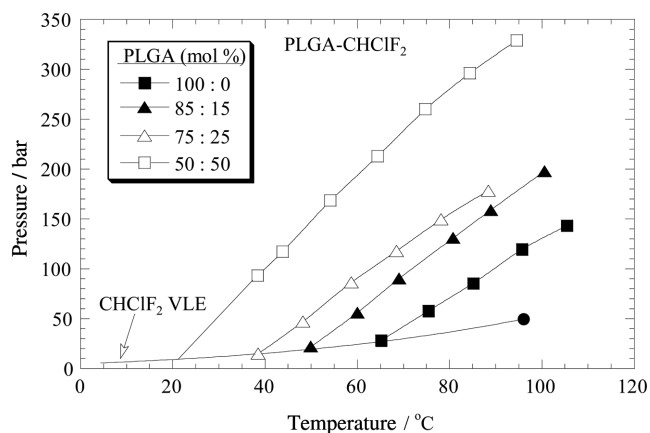


Fig. 5. Impact of glycolide content on the phase behavior of PLA, PLGA<sub>15</sub>, PLGA<sub>25</sub> and PLGA<sub>50</sub> in supercritical CHClF<sub>2</sub>. The solid circle is the critical point of CHClF<sub>2</sub>. The seven cloud point curves terminate on the vapor pressure curve of CHClF<sub>2</sub>.

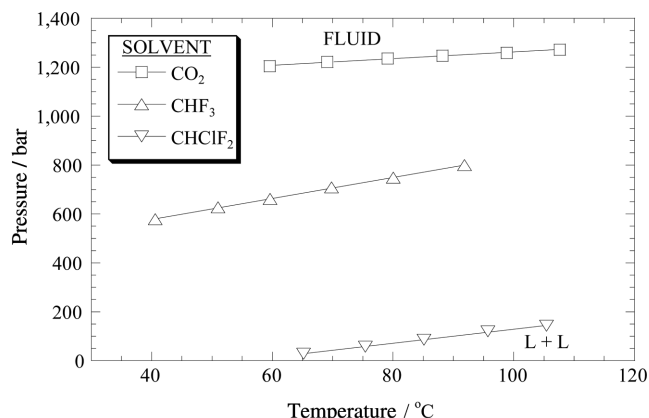


Fig. 6. Comparison of different supercritical fluid solvents for dissolving poly(d,l-lactic acid).

as shown in Table 2. The d,l-PLA-CO<sub>2</sub>-10.5 wt% CHF<sub>3</sub> system exhibits LCST type phase behavior to positive slope in 3.6 bar/°C. The cloud-point pressure decreases as the temperature decreases in the range from 42 to 94 °C. With 28.6 wt% CHF<sub>3</sub> in solution, the cloud-point pressure curve shows the LCST behavior of positive slope (4.5 bar/°C) at pressures from 610 bar to 830 bar and at temperature range of 40 to 90 °C.

Fig. 5 shows a pressure-temperature diagram of phase behavior for d,l-PLA, PLGA<sub>15</sub>, PLGA<sub>25</sub> and PLGA<sub>50</sub> in CHClF<sub>2</sub>. Although it is not possible to dissolve PLGA<sub>50</sub> in pure CO<sub>2</sub>, this PLGA<sub>50</sub> copolymer readily dissolves in CHClF<sub>2</sub> even at temperatures as low as 20 °C. This means that LCST behavior is sensitive to the glycolic acid concentration in PLGA. As the glycolide content in PLGA increases, the two-phase region expands. The slope of the curve reported by Lele and Shine [1994] is approximately 3.0 bar/°C and here the positive slopes of the cloud point curves are 2.9, 3.5, 3.3, and 4.3 bar/°C for d,l-PLA, PLGA<sub>15</sub>, PLGA<sub>25</sub>, and PLGA<sub>50</sub>, respectively.

Fig. 6 shows the phase behavior curve of d,l-PLA dissolved in supercritical CO<sub>2</sub>, CHF<sub>3</sub> and CHClF<sub>2</sub>. The cloud-point behavior for d,l-PLA-CO<sub>2</sub> (1.4 bar/°C), -CHF<sub>3</sub> (4.3 bar/°C) and -CHClF<sub>2</sub> (2.9 bar/°C) system exhibits lower critical solution temperature (LCST) curves with a positive slope. The d,l-PLA-CO<sub>2</sub> system is presented at the temperature range of 59–107 °C and pressure up to 1,270 bar. The d,l-PLA-CHF<sub>3</sub> mixture shows at the temperature from 59 to 107 and the pressure range of 579–800 bar. Also, the d,l-PLA-CHClF<sub>2</sub> system is presented at the temperature range of 65–105 °C and the pressure from 28 to 143 bar. At 90 °C, the phase behavior boundary has shifted at ~1,250 bar (CO<sub>2</sub>), ~800 bar (CHF<sub>3</sub>) and ~100 bar (CHClF<sub>2</sub>), and it is due to the polarizability difference of CO<sub>2</sub> ( $26.5 \times 10^{-25} \text{ cm}^3$ ) and CHClF<sub>2</sub> ( $44.4 \times 10^{-25} \text{ cm}^3$ ). Also, the CHF<sub>3</sub> system shows at 1,250 bar (CO<sub>2</sub>) and 800 bar (CHF<sub>3</sub>), and it is due to the dipole moment difference of CO<sub>2</sub> (0.0 Debye) and CHF<sub>3</sub> (1.6 Debye). As shown in Table 2, it seems to be due to polarizability and dipole moment difference for the CO<sub>2</sub>, CHF<sub>3</sub> and CHClF<sub>2</sub>. The pressure difference for d,l-PLA-CO<sub>2</sub>, d,l-PLA-CHF<sub>3</sub> and d,l-PLA-CHClF<sub>2</sub> mixture is considered by means of polarity factor. Very low pressures are needed to dissolve the PLGA copolymers in contrast to the kilobar pressures needed with CO<sub>2</sub> and near-kilobar pressures needed with CHF<sub>3</sub>, even though both CHClF<sub>2</sub> and CHF<sub>3</sub> have similar

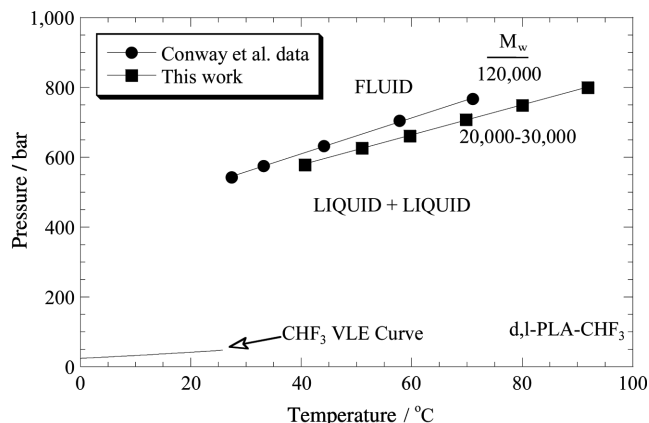


Fig. 7. Effect of weight average molecular weight for experiment data and Conway et al. data [2001] on the phase behavior of poly(d,l-lactic acid) in supercritical CHF<sub>3</sub>.

dipole moments. However, CHClF<sub>2</sub> is a better solvent for PLGA than CHF<sub>3</sub>, since it has a larger polarizability than the other two SCF solvents and also it has hydrogen that is probably more acidic than the hydrogen in CHF<sub>3</sub>.

Fig. 7 shows the effect of weight average molecular weight on the phase behavior of d,l-PLA in supercritical CHF<sub>3</sub>. The cloud-point curve exhibits LCST type behavior of the positive slope in 5.2 bar/°C (Conway et al.) and 4.3 bar/°C (this work). As shown in Fig. 7, the pressure difference of two curves is presented at about 50 bar and at temperature of 60 °C. This difference seems to be due to weight average molecular weight ( $M_w$ ) difference.

Fig. 8 shows the impact of glycolic acid content on the phase behavior of d,l-PLA and PLGA<sub>25</sub> in pure supercritical CHF<sub>3</sub>. It is clear that adding 25 mol% glycolide to the backbone of PLA shifts the CHF<sub>3</sub> cloud point pressures by as much as ~700 bar at 40 °C. The cloud-point curves of PLGA-CHF<sub>3</sub> system show similarly the phase behavior for PLGA-CO<sub>2</sub> mixture in Fig. 2. The pressure curve of PLGA<sub>25</sub>-CHF<sub>3</sub> system increases as a glycolic acid (25 mol%) concentration increase. The PLGA<sub>25</sub>-CHF<sub>3</sub> curve exhibits LCST type with a positive slope (2.5 bar/°C) at pressures from 1,300 bar to 1,430 bar and a temperature range of 40–92 °C.

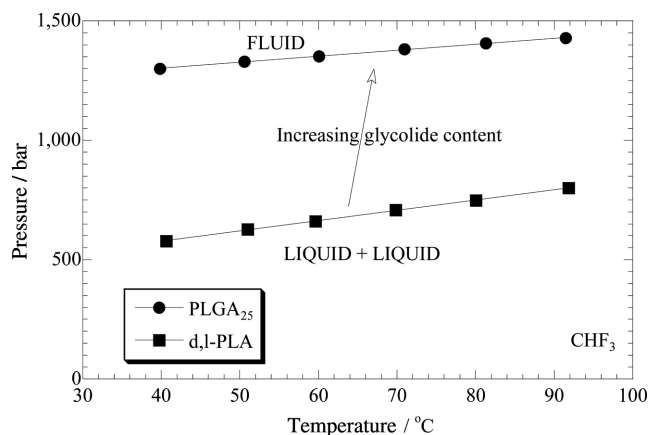


Fig. 8. Impact of glycolide content on the phase behavior of d,l-PLA and PLGA<sub>25</sub> in pure supercritical CHF<sub>3</sub>.

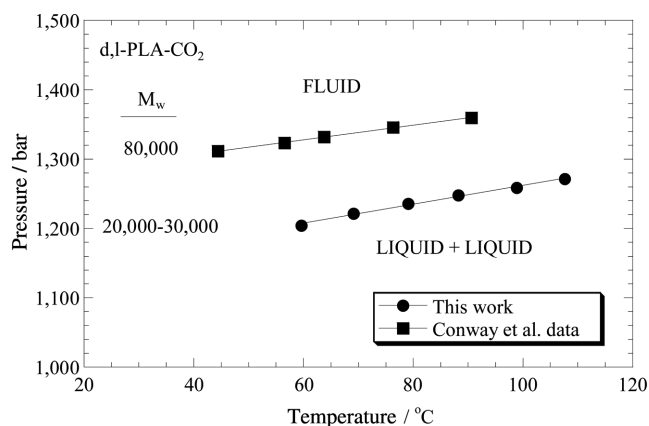


Fig. 9. Comparison of weight average molecular weight for experiment data and Conway et al. data [12] on the phase behavior of poly(d,l-lactide) in supercritical  $\text{CO}_2$ .

This shift is not quite as large as that observed with  $\text{CO}_2$  as shown in Fig. 2. Both  $\text{CO}_2$  and  $\text{CHF}_3$  have approximately the same polarizability, and also both of them have some polarity, that is,  $\text{CHF}_3$  has a dipole moment of 1.6 Debye and  $\text{CO}_2$  does a quadrupole moment of  $-4.3 \times 10^{-26} \text{ erg}^{1/2} \text{ cm}^{5/2}$ . However,  $\text{CHF}_3$  has an acidic proton that is capable of hydrogen bonding with the ester groups in PLGA, whereas  $\text{CO}_2$  is not expected to form any type of complex with PLGA. More than likely, the ability of  $\text{CHF}_3$  to form a complex with PLGA makes it a better solvent than  $\text{CO}_2$  especially since any change in favorable energetic interactions is magnified in these dense SCF solvents.

Fig. 9 shows the impact of  $M_w$  for experimental data and Conway et al. data [9] on the phase behavior of the d,l-PLA- $\text{CO}_2$  system. These cloud point curves exhibit an LCST type of slight positive slope in  $1.1 \text{ bar}^\circ\text{C}$  ( $M_w=80,000$ ) and  $1.4 \text{ bar}^\circ\text{C}$  ( $M_w=20,000-30,000$ ). The two cloud point curves in Fig. 9 are separated by approximately 110 bar for the molecular weight difference of  $\sim 55,000$  as compared to the pressure difference of 900 bar between the d,l-PLA and  $\text{PLGA}_{25}$  curves in Fig. 2.

Fig. 10 shows the impact of Mw and polymers on cloud-point behavior of d,l-PLA and poly(l-lactide)[l-PLA] in supercritical

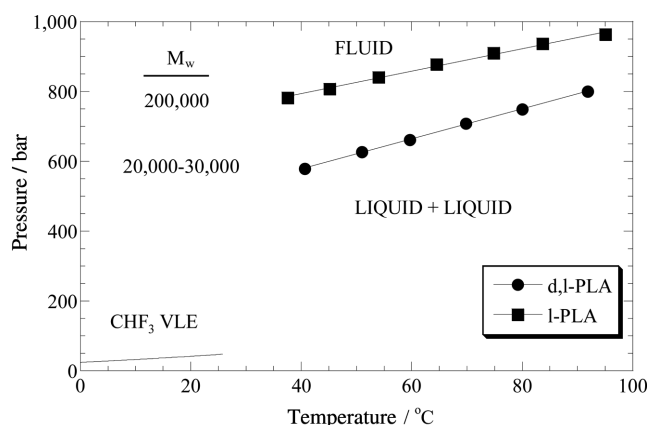


Fig. 10. Impact of weight average molecular weight on the phase behavior of poly(d,l-lactide) [d,l-PLA] and poly(l-lactide) [l-PLA] in supercritical  $\text{CHF}_3$ .

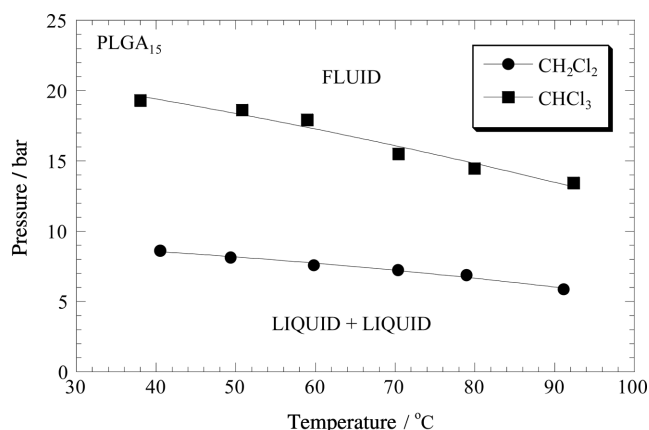


Fig. 11. Comparison of different supercritical fluid solvents ( $\text{CH}_2\text{Cl}_2$  and  $\text{CHCl}_3$ ) for dissolving  $\text{PLGA}_{15}$ .

$\text{CHF}_3$ . The pressure difference shows approximately 200 bar for a molecular weight difference of about 175,000 between the d,l-PLA- $\text{CHF}_3$  and l-PLA- $\text{CHF}_3$  mixture. Also, The two phase behavior curves exhibit the LCST type of positive slope in  $3.2 \text{ bar}^\circ\text{C}$  (l-PLA) and  $4.3 \text{ bar}^\circ\text{C}$  (d,l-PLA).

Fig. 11 shows the impact of cloud-point for the  $\text{PLGA}_{15}$ - $\text{CH}_2\text{Cl}_2$  and  $\text{PLGA}_{15}$ - $\text{CHCl}_3$  mixture at temperature range of  $\sim 40-90^\circ\text{C}$  and at lower pressure below  $\sim 20$  bar.

The phase behavior difference is due to dipole moment 1.1 D ( $\text{CHCl}_3$ ) and 1.8 D ( $\text{CH}_2\text{Cl}_2$ ). These two cloud-point curves exhibit UCST type behavior of a negative slope in  $-0.05 \text{ bar}^\circ\text{C}$  ( $\text{CH}_2\text{Cl}_2$ ) and  $-0.12 \text{ bar}^\circ\text{C}$  ( $\text{CHCl}_3$ ) at lower pressure.

## CONCLUSIONS

$\text{CO}_2$  is a poor quality solvent for PLGA (glycolide=0.0, 15, 25 and 50 wt%) copolymers. Particularly, it is impossible for the  $\text{PLGA}_{50}$ - $\text{CO}_2$  mixture to dissolve at temperature to  $120^\circ\text{C}$  and pressures up to 2,800 bar. The phase behavior for d,l-PLA- $\text{CO}_2$ ,  $\text{PLGA}_{15}$ - $\text{CO}_2$  and  $\text{PLGA}_{25}$ - $\text{CO}_2$  system exhibits UCST region curve with negative slope in  $-0.6 \text{ bar}^\circ\text{C}$  ( $\text{PLGA}_{15}$ ) and  $-2.6 \text{ bar}^\circ\text{C}$  ( $\text{PLGA}_{25}$ ), and LCST curve with positive slope in  $1.4 \text{ bar}^\circ\text{C}$  (d,l-PLA). As the glycolide concentration in the backbone increases, the phase behavior pressure increases substantially to obtain a single phase. The effect of glycolide and weight average molecular weight on the cloud point pressure is significant of the effect with supercritical  $\text{CO}_2$ ,  $\text{CHClF}_2$ ,  $\text{CHF}_3$ ,  $\text{CHCl}_3$  and  $\text{CH}_2\text{Cl}_2$ . The differences in the phase behavior exhibited by the d,l-PLA-,  $\text{PLGA}_{15}$ -,  $\text{PLGA}_{25}$ - and  $\text{PLGL}_{50}$ -SCF solvent systems are related to those in intermolecular interactions between the components in the solution. The  $\text{CHClF}_2$  data strongly suggest that a polar cosolvent capable of hydrogen bonding to the ester linkage in PLGA (0.0-50 mol%) is needed if low pressure, single-phase processing of this copolymer is desired.

However, d,l-PLA,  $\text{PLGA}_{15}$ ,  $\text{PLGA}_{25}$  and  $\text{PLGL}_{50}$  polymers can be intimately mixed with a variety of insoluble materials at low pressures in pure  $\text{CO}_2$  since the glass transition temperature of the biodegradable polymer is significantly lowered by the plasticization effect of supercritical  $\text{CO}_2$ .

## ACKNOWLEDGMENT

This work was supported by a grant No. R05-2001-000-01177-0 from Korea Science & Engineering Foundation. The author gratefully acknowledges the financial support from the Korea Ministry of Commerce, Industry & Energy and the Korea Energy Management Corporation.

## REFERENCES

- Benedetti, L., Bertucco, A. and Pallado, P., "Production of micronic particles of biocompatible polymer using supercritical carbon dioxide," *Biotechnol. Bioeng.*, **53**, 232 (1997).
- Benson, R. C. and Flygare, W. H., "The molecular zeeman effect in propene and comparison of the magnetic susceptibility anisotropies with cyclopropane and other small ring compounds," *Chem. Phys. Lett.*, **4**, 141 (1969).
- Bodmeier, R., Wang, H., Dixon, D. J., Mawson, S. and Johnson, K. P., "Polymeric microspheres prepared by spraying into compressed carbon dioxide," *Pharm. Res.*, **12**, 1211 (1995).
- Byun, H. S. and McHugh, M. A., "Impact of "Free" monomer concentration on the phase behavior of supercritical carbon dioxide-polymer mixtures," *Ind. Eng. Chem. Res.*, **39**, 4658 (2000).
- Conway, S. E., Byun, H. S., McHugh, M. A., Wang, J. D. and Mandel, F. S., "Poly(lactide-co-glycolide) solution in supercritical CO<sub>2</sub>, CHF<sub>3</sub>, and CHClF<sub>2</sub>," *J. Appl. Polym. Sci.*, **80**, 1155 (2001).
- Daubert, T. E. and Danner, R. P., *Physical and thermodynamic properties of pure chemicals*, Hemisphere Publishing, NY (1989).
- Kim, J. H., Paxton, T. E. and Tomasko, D. L., "Microencapsulation of naproxen using rapid expansion of supercritical solutions," *Biotechnol. Prog.*, **12**, 650 (1996).
- Kirby, C. F. and McHugh, M. A., "Phase behavior of polymers in supercritical fluid solvents," *Chem. Rev.*, **99**, 565 (1999).
- Kuk, Y. M., Lee, B. C., Lee, Y. W. and Lim, J. S., "High-pressure phase behavior of poly(D,L-lactide) in chlorodifluoromethane, difluoromethane, trifluoromethane, and 1,1,1,2-tetrafluoroethane," *J. Chem. Eng. Data*, **47**, 575 (2002).
- Lee, B. C., "Solvent power dependence of phase behavior of biodegradable polymers in high-pressure hydrofluorocarbons," *Korean J. Chem. Eng.*, **20**, 542 (2003).
- Lee, J. W., Kim, D. Y. and Lee, H., "Phase behavior and structure transition of the mixed methane and nitrogen hydrates," *Korean J. Chem. Eng.*, **23**, 299 (2006).
- Lele, A. and Shine, A. D., "Effect of RESS dynamics on polymer morphology," *Ind. Eng. Chem. Res.*, **33**, 1476 (1994).
- Mandel, F. S. and Wang, J. D., "Manufacturing of specialty materials in supercritical fluid carbon dioxide," *Inorg. Chim. Acta.*, **294**, 214 (1999).
- McHugh, M. A. and Krukonis, V. J., *Supercritical fluid extraction: principles and practice*, 2nd ed., Butterworth, Boston, MA (1994).
- Meyer, G. and Toennies, J. P., "Determination of quadrupole moments of light hydrocarbon molecules from rotationally inelastic state scattering cross sections," *Chem. Phys.*, **52**, 39 (1980).
- Middleton, J. C. and Tipton, A. J., *Synthetic biodegradable polymers as medical devices*, Medical Plastics and Biomaterials Magazine, March/April (1998).
- Park, J. Y., Lim, J. S., Park, K. H. and Yoo, K. P., "Phase behavior of poly(L-lactide) and polycaprolactone in various solvents at high pressure," *Korean Chem. Eng. Res.*, **42**, 317 (2004).
- Prausnitz, J. M., Lichtenthaler, R. N. and de Azevedo, E. G., *Molecular thermodynamics of fluid-phase equilibria*, 2nd ed., Prentice-Hall, Englewood Cliffs, NJ (1986).
- Reid, R. C., Prausnitz, J. M. and Polling, B. E., *The properties of gases and liquids*, 4th ed., McGraw-Hill, New York, NY (1987).