

## Hydrogen production by steam reforming of LNG over Ni/Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> catalysts: Effect of ZrO<sub>2</sub> and preparation method of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub>

Jeong Gil Seo, Min Hye Youn, Sunyoung Park, Joohyung Lee, Sang Hee Lee, Howon Lee and In Kyu Song<sup>†</sup>

School of Chemical and Biological Engineering, Research Center for Energy Conversion and Storage,  
Seoul National University, Shinlim-dong, Gwanak-gu, Seoul 151-744, Korea

(Received 22 April 2007 • accepted 11 June 2007)

**Abstract**—An Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> support was prepared by grafting a zirconium precursor onto the surface of commercial  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. A physical mixture of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> was also prepared for the purpose of comparison. Ni/Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> catalysts were then prepared by an impregnation method, and were applied to the hydrogen production by steam reforming of liquefied natural gas (LNG). The effect ZrO<sub>2</sub> and preparation method of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> on the performance of supported nickel catalysts in the steam reforming of LNG was investigated. The Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> prepared by a grafting method was more efficient as a support for nickel catalyst than the physical mixture of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> in the hydrogen production by steam reforming of LNG. The well-developed tetragonal phase of ZrO<sub>2</sub> and the high dispersion of ZrO<sub>2</sub> on the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> were responsible for the enhanced catalytic performance of Ni/Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> prepared by way of a grafting method.

Key words: Hydrogen, Liquefied Natural Gas (LNG), Steam Reforming, Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub>, Supported Nickel Catalyst

### INTRODUCTION

Hydrogen has attracted considerable attention as a promising energy due to its potential applicability in fuel cell systems [1-5]. Therefore, reforming technologies for the production of hydrogen have been extensively studied [6-12]. Among these, steam reforming has been recognized as a feasible method to produce hydrogen from liquefied natural gas (LNG). The extensive piping system for LNG in modern cities makes LNG well suited as a hydrogen source for residential reformers.

Nickel-based catalysts have been widely studied in the steam reforming of LNG although nickel-based catalysts require a high reaction temperature and an excess amount of steam to prevent coke deposition on the catalyst surface [13-15]. However, it has been reported that ZrO<sub>2</sub> support enhances the adsorption of steam onto its surface and activates the gasification of hydrocarbons adsorbed on the catalyst surface in the steam reforming reactions, resulting in an enhancement in hydrogen production and coke resistance [16,17]. Therefore, the addition of ZrO<sub>2</sub> into the conventional nickel-based catalysts can be a promising choice to improve the performance of the nickel-based catalysts.

In this work, an Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> support was prepared by grafting a zirconium precursor onto the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. For the purpose of comparison, a physical mixture of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> was also prepared. Ni/Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> and Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts were then prepared by an impregnation method for use in hydrogen production by steam reforming of LNG. The effect of ZrO<sub>2</sub> and preparation method of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> on the performance of supported nickel catalysts in the steam reforming of LNG was investigated.

### EXPERIMENTAL

<sup>†</sup>To whom correspondence should be addressed.

E-mail: inksong@snu.ac.kr

An Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> support was prepared by grafting an appropriate amount of zirconium precursor onto the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> [17-19]. A known amount of alumina ( $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, Degussa) was added to 100 ml of anhydrous toluene (Aldrich) for uniform dispersion, and an excess amount of triethylamine (TEA, Fluka) was then added to the alumina slurry to activate the hydroxyl groups on the alumina surface. An appropriate amount of zirconium precursor (Zr(OBu)<sub>4</sub>, Aldrich) was slowly added to the slurry with constant stirring for 1 h, and the resulting slurry was stirred at room temperature for 6 h to achieve the complete reaction of the activated surface hydroxyl groups of alumina with the butoxide groups of zirconium precursor. After removing the unreacted zirconium precursor and butanol (by-product) by centrifugation, the slurry was washed several times with anhydrous toluene. Upon the addition of an excess amount of deionized water to the washed slurry, a white gel was formed. After maintaining the white gel in deionized water for 6 h, a solid product was obtained by filtration. The solid product was dried overnight at 120 °C, and then calcined at 700 °C for 5 h to yield the Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> support (denoted as AZ-graft). A physical mixture of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> was also prepared by a direct hydrolysis of zirconium precursor (Zr(OBu)<sub>4</sub>, Aldrich) onto the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (Degussa) for the purpose of comparison (denoted as AZ-mix). The supported nickel catalysts were then prepared by impregnating known amounts of a nickel precursor (Ni(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O, Aldrich) onto the supports. The prepared catalysts were denoted as Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, Ni/AZ-graft, and Ni/AZ-mix. The nickel loading was fixed at 20 wt% in all cases.

In order to investigate reducibility of the supported nickel catalysts, temperature-programmed reduction (TPR) measurements were carried out in a conventional flow system with a moisture trap connected to a thermal conductivity detector (TCD) at temperatures ranging from room temperature to 1,000 °C with a ramping rate of 5 °C/min. For the TPR measurements, a mixed stream of H<sub>2</sub> (2 ml/min) and N<sub>2</sub> (20 ml/min) was used for 0.1 g of catalyst sample.

Steam reforming of LNG was carried out in a continuous flow

**Table 1. Chemical compositions of supports determined by ICP-AES analyses**

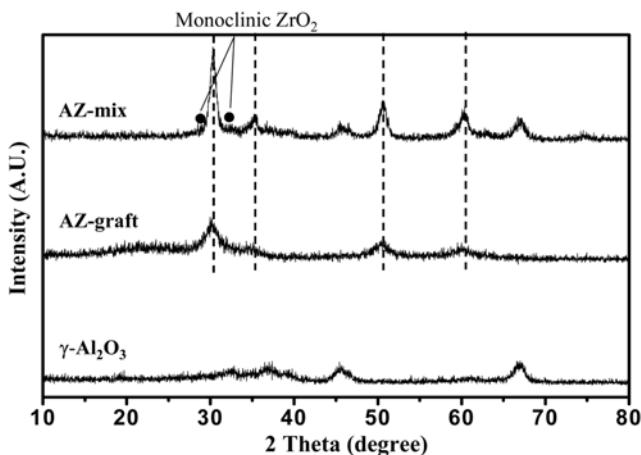
Support	Zr loading (wt%)	Zr/Al atomic ratio
$\gamma\text{-Al}_2\text{O}_3$	0	0
AZ-graft	21.9	0.17
AZ-mix	20.7	0.16

fixed-bed reactor. Each catalyst was pretreated with a mixed stream of  $\text{H}_2$  (10 ml/min) and  $\text{N}_2$  (30 ml/min) at 800 °C for 3 h. Water was sufficiently vaporized by passing through a pre-heating zone and continuously fed into the reactor together with LNG (92 vol%  $\text{CH}_4$  and 8.0 vol%  $\text{C}_2\text{H}_6$ ) and  $\text{N}_2$  carrier (30 ml/min). The steam reforming of LNG was conducted at 600 °C. The steam/carbon ratio was fixed at 2.0, and the total feed flow rate was maintained at 27,000 ml·h<sup>-1</sup>/g-catalyst. The reaction products were periodically sampled and analyzed using an on-line gas chromatograph (Younglin, ACME 6000) equipped with a TCD.

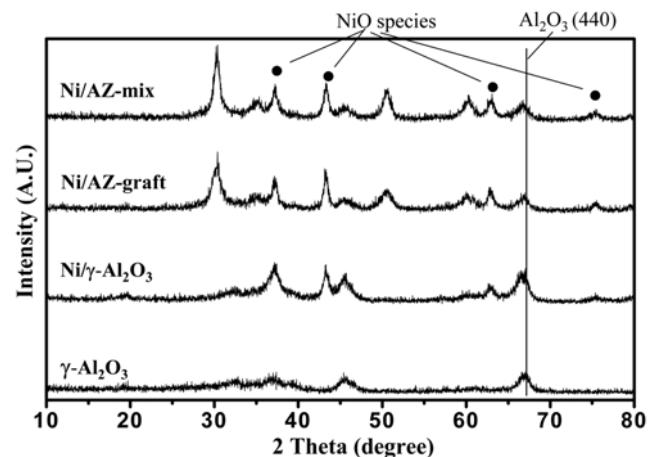
## RESULTS AND DISCUSSION

Table 1 shows the chemical compositions of AZ-graft and AZ-mix supports determined by ICP-AES analyses. The Zr/Al atomic ratio of AZ-graft was found to be 0.17, indicating that  $\text{Al}_2\text{O}_3\text{-ZrO}_2$  support was successfully prepared by a grafting method. For the purpose of comparison, the Zr/Al atomic ratio of AZ-mix was intentionally adjusted to have a similar value to that of AZ-graft.

Fig. 1 shows the XRD patterns of supports. Dashed lines in Fig. 1 represent the tetragonal phase of zirconia. It was found that AZ-graft retained pure tetragonal phase of zirconia, while AZ-mix had both monoclinic phase and tetragonal phase of zirconia. Furthermore, AZ-graft showed relatively broader diffraction peaks of zirconia than AZ-mix. This indicates that zirconia was highly dispersed in the AZ-graft by the reaction between activated hydroxyl groups of alumina and zirconium precursor, resulting in the formation of an  $\text{Al}_2\text{O}_3\text{-ZrO}_2$  composite structure. It is believed that the metastable tetragonal phase of zirconia was stabilized by its incorporation into the lattice of alumina in the AZ-graft support. In the AZ-mix support, on the other hand, zirconium precursor was easily

**Fig. 1. XRD patterns of  $\gamma\text{-Al}_2\text{O}_3$ , AZ-graft, and AZ-mix supports.**

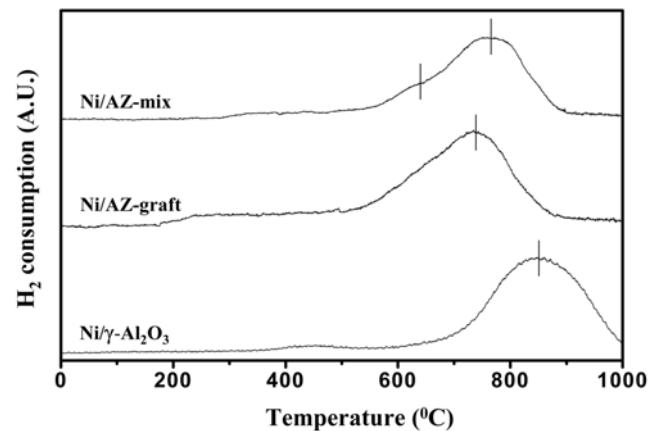
January, 2008

**Fig. 2. XRD patterns of  $\text{Ni}/\gamma\text{-Al}_2\text{O}_3$ , Ni/AZ-graft, and Ni/AZ-mix catalysts.**

aggregated during the hydrolysis and condensation steps. This means that the particle size of zirconia in the AZ-mix exceeded the critical size for causing a phase transformation of zirconia from the tetragonal phase to the monoclinic phase.

Fig. 2 shows the XRD patterns of supported nickel catalysts. All the supported nickel catalysts showed the diffraction peaks corresponding to NiO species. A noticeable point is that the (440) diffraction peak of alumina in the  $\text{Ni}/\gamma\text{-Al}_2\text{O}_3$  and Ni/AZ-mix catalysts slightly shifted to a lower angle. This indicates that  $\text{Ni}^{2+}$  was incorporated into the lattice of  $\gamma\text{-Al}_2\text{O}_3$ , resulting in the increment of lattice parameter of alumina in the  $\text{Ni}/\gamma\text{-Al}_2\text{O}_3$  and Ni/AZ-mix catalysts [20-22]. In the Ni/AZ-graft catalyst, however, the shift of (440) diffraction peak of alumina was not observed. It is believed that the highly dispersed  $\text{ZrO}_2$  inhibited the incorporation of  $\text{Ni}^{2+}$  into the lattice of alumina in the Ni/AZ-graft catalyst.

Fig. 3 shows the TPR profiles of supported nickel catalysts.  $\text{Ni}/\gamma\text{-Al}_2\text{O}_3$  catalyst showed a reduction band at around 850 °C, which was attributed to the reduction of nickel aluminate. On the other hand, Ni/AZ-graft catalyst showed a reduction band at around 730 °C, which was believed to be due to the reduction of NiO species strongly interacted with support. These results indicate that the grafted  $\text{ZrO}_2$

**Fig. 3. TPR profiles of  $\text{Ni}/\gamma\text{-Al}_2\text{O}_3$ , Ni/AZ-graft, and Ni/AZ-mix catalysts.**

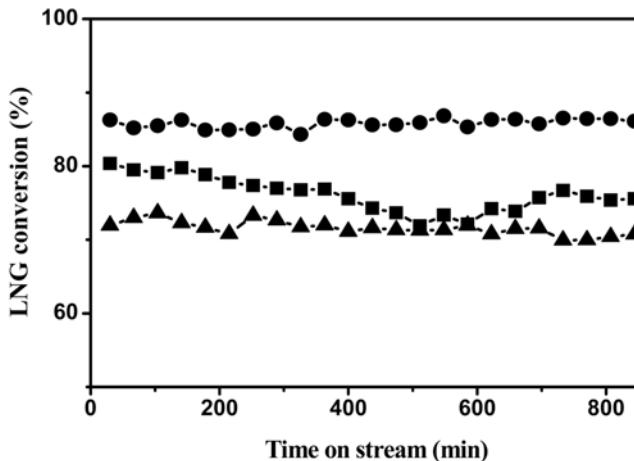


Fig. 4. LNG conversions with time on stream at 600 °C ( $\blacktriangle$ =Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>,  $\blacksquare$ =Ni/AZ-mix,  $\bullet$ =Ni/AZ-graft).

inhibited the formation of nickel aluminate species through the formation of a favorable Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> composite structure. Ni/AZ-mix catalyst showed a shoulder at around 620 °C along with a main reduction band at around 760 °C. This means that nickel species were supported not only on the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> but also on the surface of ZrO<sub>2</sub> in the Ni/AZ-mix catalyst. Among the catalysts tested, the Ni/AZ-graft showed the highest reducibility.

Fig. 4 shows the LNG conversions with time on stream in the steam reforming of LNG at 600 °C. The LNG conversions were decreased in the order of Ni/AZ-graft>Ni/AZ-mix>Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, in good agreement with the trend of reducibility. Both Ni/AZ-graft and Ni/AZ-mix catalysts showed a higher LNG conversion than Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. This may be explained by the steam adsorption capability of ZrO<sub>2</sub>. It is well known that methane is adsorbed on the surface of metallic nickel, while steam is adsorbed not only on the metallic nickel but also on the support [16]. The adsorbed steam, therefore, should migrate to the nickel surface for the steam reforming reaction. Steam adsorption capability of support is very important, because nickel-based catalysts catalyze not only steam reforming reaction but also carbon deposition. The above results strongly support that the Ni/AZ-graft and Ni/AZ-mix catalysts retained a higher steam adsorption capability than the Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalyst. The Ni/AZ-graft catalyst showed a higher LNG conversion than the Ni/AZ-mix catalyst, because ZrO<sub>2</sub> was highly dispersed on the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> in the Ni/AZ-graft catalyst. The hydrogen compositions (dry gas basis) over the supported nickel catalysts after the 800 min-reaction decreased in the order of Ni/AZ-graft (69.2%)>Ni/AZ-mix (67.8%)>Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (65.8%). The CO compositions (dry gas basis) decreased in the order of Ni/AZ-graft (11.5%)>Ni/AZ-mix (11.2%)>Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (10.2%), and the CO<sub>2</sub> compositions (dry gas basis) also decreased in the order of Ni/AZ-graft (15.8%)>Ni/AZ-mix (15.6%)>Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (15.5%). It is concluded that the well-developed tetragonal phase of ZrO<sub>2</sub> and the high dispersion of ZrO<sub>2</sub> on the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> were responsible for the enhanced catalytic performance of Ni/AZ-graft. A new interaction between nickel and ZrO<sub>2</sub> inhibiting the incorporation of nickel into the lattice of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> through the formation of a favorable Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> composite structure was also responsible for the enhanced catalytic performance of Ni/AZ-

graft.

## CONCLUSIONS

An Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> support was prepared by grafting a zirconium precursor onto the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. For the purpose of comparison, a physical mixture of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> was also prepared. Ni/Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> catalysts were then prepared by an impregnation method for use in the hydrogen production by steam reforming of LNG. The effect of ZrO<sub>2</sub> and preparation method of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> on the performance of supported nickel catalysts in the steam reforming of LNG was investigated. The highly dispersed ZrO<sub>2</sub> inhibited the incorporation of nickel species into the lattice of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> through the formation of a favorable Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> composite structure in the Ni/AZ-graft catalyst. In the hydrogen production by steam reforming of LNG, the LNG conversions and hydrogen compositions were decreased in the order of Ni/AZ-graft>Ni/AZ-mix>Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, in good agreement with the trend of reducibility. The well-developed tetragonal phase of ZrO<sub>2</sub> and the high dispersion of ZrO<sub>2</sub> on the surface of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> played an important role in the adsorption of steam and the subsequent spillover of steam from the support to the active nickel in the Ni/AZ-graft catalyst.

## ACKNOWLEDGMENTS

The authors wish to acknowledge support from the Seoul Renewable Energy Research Consortium (Seoul R & BD Program) and RCECS (Research Center for Energy Conversion and Storage: R11-2002-102-00000-0).

## REFERENCES

1. B.-G Park, *Korean J. Chem. Eng.*, **21**, 782 (2004).
2. D. J. Moon, J. W. Ryu, S. D. Lee and B. S. Ahn, *Korean J. Chem. Eng.*, **19**, 921 (2002).
3. D. J. Moon, K. Sreekumar, S. D. Lee, B. G Lee and H. S. Kim, *Appl. Catal. A*, **215**, 1 (2006).
4. Q. Ming, T. Healey, L. Allen and P. Irving, *Catal. Today*, **77**, 51 (2002).
5. S. Y. Lee, J. H. Kwak, M. S. Kim, S. W. Nam, T. H. Lim, S.-A. Hong and K. J. Yoon, *Korean J. Chem. Eng.*, **24**, 226 (2007).
6. J. K. Lee and D. Park, *Korean J. Chem. Eng.*, **15**, 658 (1998).
7. A. Praharsa, A. Adesina, D. L. Trimm and N. W. Cant, *Korean J. Chem. Eng.*, **20**, 468 (2003).
8. S. J. Kong, J. H. Jun and K. J. Yoon, *Korean J. Chem. Eng.*, **21**, 793 (2004).
9. J. Zhang, Y. Wang, R. Ma and D. Wu, *Korean J. Chem. Eng.*, **20**, 288 (2003).
10. E. Promaros, S. Assabumrungrat, N. Laosiripojana, P. Praserthdam, T. Takawa and S. Goto, *Korean J. Chem. Eng.*, **24**, 44 (2007).
11. K. H. Kim, S. Y. Lee and K. J. Yoon, *Korean J. Chem. Eng.*, **23**, 356 (2006).
12. S. W. Nam, S. P. Yoon, H. Y. Ha, S.-A. Hong and A. P. Maganyuk, *Korean J. Chem. Eng.*, **17**, 288 (2000).
13. J. N. Armor, *Appl. Catal. A*, **176**, 159 (1999).
14. J. Sehested, *Catal. Today*, **111**, 103 (2006).
15. J. Sehested, A. Carlsson, T. V. W. Janssens, P. L. Hansen and A. K.

- Datye, *J. Catal.*, **197**, 200 (2001).
16. Y. Matsumura and T. Nakamori, *Appl. Catal. A*, **258**, 107 (2004).
17. J. G. Seo, M. H. Youn and I. K. Song, *J. Mol. Catal. A*, **268**, 9 (2007).
18. M. V. Landau, E. Dafa, M. L. Kaliya, T. Sen and M. Herskowitz, *Micro. Meso. Mater.*, **49**, 65 (2001).
19. P. Iengo, M. D. Serio, V. Solinas, D. Gazzoli, G. Salvio and E. Santacesaria, *Appl. Catal. A*, **170**, 225 (1998).
20. J. A. Wang, A. Morales, X. Bokhimi and O. Novaro, *Chem. Mater.*, **11**, 308 (1999).
21. A. Corma, V. Fornes, R. M. Aranda and F. Rey, *J. Catal.*, **134**, 58 (1992).
22. E. D. Dimotakis and T. J. Pinnavaia, *Inorg. Chem.*, **29**, 2393 (1990).